



## Green Machining for the Dry Milling Process of Stainless Steel 304

Journal:	<i>Part B: Journal of Engineering Manufacture</i>
Manuscript ID	JEM-19-0310.R1
Manuscript Type:	Original article
Date Submitted by the Author:	n/a
Complete List of Authors:	Thanh, Nguyen; Duy Tan University, Institute of Research and Development; Le Quy Don Technical University, Faculty of Mechanical Engineering Mia, Mozammel; Ahsanullah University of Science and Technology, Mechanical and Production Engineering Dang, Xuan-Phuong; Nha Trang University Le-Chi, Hieu; University of Greenwich, Faculty of Engineering and Science Packianather, Michael; Cardiff University
Keywords:	Dry milling, Power factor, Energy consumption, Surface roughness, Principal component analysis, Radial basis function
Abstract:	Dry machining represents an eco-friendly method that reduces the environmental impacts, saves energy costs, and protects operator health. This paper presents a multi-response optimization which aims to enhance the power factor and decrease the energy consumption as well as the surface roughness for the dry machining of a stainless steel 304. The cutting speed ( $V$ ), depth of cut ( $a$ ), feed rate ( $f$ ), and nose radius ( $r$ ) were the processing conditions. The outputs of the optimization are the power factor, energy consumption, and surface roughness. The relationships between inputs and outputs were established using the radial basis function models. The experimental data were normalized, with the use of the grey relational analysis. The principal component analysis is applied to calculate the weight values of technical responses. The desirability approach is used to observe the optimal values. The results showed that the technical outputs are primarily influenced by the feed rate and cutting speed. The reductions of energy consumption and surface roughness are approximately 34.9 % and 57.7 %, respectively, and the power factor improves around 28.8 %, compared to the initial

1  
2  
3  
4  
5  
6  
7  
8  
9  
10  
11  
12  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

	process parameter settings. The outcomes and findings of the investigated work can be used for further research in sustainable design and manufacturing as well as directly used in the knowledge-based and expert systems for dry milling applications in industrial practices.



## Title Page

**Article type:** Research article

**Corresponding author:**

**Trung-Thanh Nguyen**

Institute of Research and Development, Duy Tan University, 03 Quang Trung, Da Nang 550000, Vietnam

Faculty of Mechanical Engineering, Le Quy Don Technical University, 236 Hoang Quoc Viet, Ha Noi 100000, Viet Nam

E-mail addresses: [nguyentrongthanh6@duytan.edu.vn](mailto:nguyentrongthanh6@duytan.edu.vn);

[trungthanhk21@mta.edu.vn](mailto:trungthanhk21@mta.edu.vn)

ORCID: 0000-0002-0838-872X

**Article title:** *Green Machining for the Dry Milling Process of Stainless Steel 304*

**Authors:**

**Trung-Thanh Nguyen<sup>1,2\*</sup>, Mozammel Mia<sup>3</sup>, Xuan-Phuong Dang<sup>4</sup>, Chi-Hieu Le<sup>5</sup>, Michael Packianather<sup>6</sup>**

<sup>1</sup>Institute of Research and Development, Duy Tan University, 03 Quang Trung, Da Nang 550000, Vietnam

<sup>2</sup>Faculty of Mechanical Engineering, Le Quy Don Technical University, 236 Hoang Quoc Viet, Ha Noi 100000, Viet Nam

<sup>3</sup> Mechanical and Production Engineering, Ahsanullah University of Science and Technology, Dhaka, Bangladesh

<sup>4</sup>Faculty of Mechanical Engineering, Nha Trang University, Nguyen Dinh Chieu, Nha Trang 57000, Viet Nam

<sup>5</sup>Faculty of Engineering & Science, University of Greenwich, Chatham, UK

<sup>6</sup>School of Engineering, Cardiff University, Cardiff, UK

**Keywords:**

Dry milling; Power factor; Energy consumption; Surface roughness; Principal component analysis; Radial basis function.

## Green Machining for the Dry Milling Process of Stainless Steel 304

### Abstract:

Dry machining represents an eco-friendly method that reduces the environmental impacts, saves energy costs, and protects operator health. This paper presents a multi-response optimization which aims to enhance the power factor and decrease the energy consumption as well as the surface roughness for the dry machining of a stainless steel 304. The cutting speed ( $V$ ), depth of cut ( $a$ ), feed rate ( $f$ ), and nose radius ( $r$ ) were the processing conditions. The outputs of the optimization are the power factor, energy consumption, and surface roughness. The relationships between inputs and outputs were established using the radial basis function models. The experimental data were normalized, with the use of the grey relational analysis. The principal component analysis is applied to calculate the weight values of technical responses. The desirability approach is used to observe the optimal values. The results showed that the technical outputs are primarily influenced by the feed rate and cutting speed. The reductions of energy consumption and surface roughness are approximately 34.85 % and 57.65 %, respectively, and the power factor improves around 28.83 %, compared to the initial process parameter settings. The outcomes and findings of the investigated work can be used for further research in sustainable design and manufacturing as well as directly used in the knowledge-based and expert systems for dry milling applications in industrial practices.

**Keywords:** Dry milling; Power factor; Energy consumption; Sustainable Manufacturing; Principal component analysis; Radial basis function.

## 1. Introduction

In wet machining, liquid coolant is normally used to reduce the temperature of both workpiece and cutting tool, as well as to evacuate chips from the cutting area, with hundreds of thousands of gallons of coolant fluid used per year, causing a lot of money spent and poor environmental impacts <sup>1</sup>. The total cost of the lubrication accounts for 7-17 % of the cutting tool cost, and it is even greater than overhead and labor costs <sup>2</sup>. Fortunately, dry machining is becoming more prevalent, especially in milling, and it is considered as one of the eco-friendly machining processes, with good environmental impacts and cost-effectiveness. With the emerging trends of sustainable design and manufacturing, dry machining is considered as one of the green solutions to enforce environmental protection laws for occupational safety and health regulations; and it is an effective solution for sustainable manufacturing, especially to help to minimize the use of lubricants that cause air and water pollutions.

The improvements in the technical parameters of dry machining processes have been considered by many researchers<sup>3-5</sup>. Fundamentally, the technical outputs of a machining process, including the surface integrity, cutting temperature, and tool life were improved by means of optimization of process parameters (or machining factors) <sup>6,7</sup>. Babu *et al.* <sup>8</sup> analyzed the surface roughness and vibration for the orthogonal milling. The temperature variations in the workpiece and cutting tool were explored for the dry machining of Inconel 718 <sup>9</sup>. The surface integrity was improved for milling processes of the Al-Zn-Mg-Cu alloy <sup>10</sup>, aluminum <sup>11</sup>, Ti-6Al-4V alloy <sup>12</sup>, and the hard turning of AISI 52100 <sup>13</sup>. The grey relational analysis (GRA) was applied to achieve optimum inputs that maximize the surface properties, energy criteria, and production rate <sup>14</sup>. Krolczyk *et al.* <sup>15</sup> found that a longer tool life can be obtained under dry cutting compared to the lubricant condition. Additionally, Baowan *et al.* <sup>16</sup> revealed that the surface roughness and tool life were significantly influenced by the cutting angle and tools. Pham *et al.* <sup>17</sup> stated that the tool-chip contact length, the workpiece vibration, and the surface roughness were increased with

1  
2  
3 increasing cutting depth and feed rate for the dry milling of A6061 aluminum alloy. Jahan *et al.*  
4  
5 <sup>18</sup> concluded that the mid-level of the feed and depth of cut could be used to decrease the tool  
6  
7 wear and surface roughness in the milling of polycarbonates. Mia and Dhar <sup>19</sup> emphasized that  
8  
9 specific cutting energy was influenced favorably by the increase in cutting speed.  
10  
11

12 Recently, the trade-off between energy consumption, surface integrity, and productivity  
13  
14 has been explored in the works of literature. As part of trade-off among responses, Khan *et al.* <sup>20</sup>  
15  
16 conducted multi-response optimization for the face milling of steel to attain improved surface  
17  
18 quality, material removal quantity and cutting energy. From conventional statistics-based  
19  
20 approaches to advanced neural and evolutionary algorithms are continually used for computation  
21  
22 of the best trade-off. For instance, Mia *et al.* <sup>21</sup> performed intelligent optimization of the  
23  
24 machining process from the perspective of smart manufacturing. On the other side, the response  
25  
26 surface methodology (RSM) was applied to analyze the impacts of input process parameters on  
27  
28 energy consumption <sup>22</sup>, power consumption, cutting force, and surface roughness <sup>23</sup>. Similarly,  
29  
30 the multi-objective optimizations were performed in order to minimize the energy consumption  
31  
32 in the dry turning of stainless steel <sup>24</sup>. Zhang *et al.* <sup>25</sup> proposed the relations between the process  
33  
34 parameters on the total processing time, specific energy consumption, and carbon emissions.  
35  
36 Song *et al.* <sup>26</sup> developed a new model to predict the machining forces in multi-axis milling. The  
37  
38 impacts of the process parameters on the machining energy for the micro-milling composites  
39  
40 were analyzed by Kuram <sup>27</sup>. The stress field distribution on a cutter in the milling of titanium  
41  
42 alloy was analyzed based on the empirical models of the milling force and the contact area  
43  
44 between the cutter and the chip <sup>28</sup>. As a result, various approximation methods and optimizing  
45  
46 techniques were used to render the relationship between the processing conditions and output  
47  
48 criteria and to find the optimum process parameter. The different performances measured were  
49  
50 optimized and improved by means of the optimum factors. However, the drawbacks of the  
51  
52 published works can be listed as bellow:  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 The outputs response parameters of the machining process such as the energy  
4 consumption, cutting forces, quality of the machined part, and tool life were widely considered  
5 in the published works. Practically, the power factor (the ratio of the active power consumption  
6 and the apparent power) is necessary to be considered as an important technical parameter for  
7 maximizing energy efficiency.  
8  
9

10  
11  
12 The stainless steels are widely used for manufacturing components used in the  
13 automotive and aerospace industry as well as in medical sector<sup>29, 30</sup>. Unfortunately, it is difficult  
14 to machine this material due to work hardening, high surface roughness, high tool wear, and low  
15 production rate. Furthermore, machining stainless steel is required higher energy consumption  
16 because of low thermal conductivity and high heat capacity. Therefore, it is necessary and  
17 important to develop optimization models to support the decision-making process and predicting  
18 the values of the power factor (PF), energy consumption (EC), and surface roughness ( $R_a$ ) for  
19 dry machining applications.  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31

32  
33 As a result, a few studies have focused on the process parameters optimization for  
34 improving the technological performances of the dry machining processes. However,  
35 optimizations of the machining process parameters and cutting tool's geometry for simultaneous  
36 improvements of the power factor (PF), energy consumption (EC), and surface roughness ( $R_a$ )  
37 have not been considered in the aforementioned works; and these were investigated and  
38 presented in details in this study. Furthermore, the optimal results directly selected from  
39 experimental data may fall into the trap of local optimization.  
40  
41  
42  
43  
44  
45  
46  
47  
48

49 In order to overcome the above-mentioned drawbacks of the published works, in this  
50 study, a multiple-response optimization of machining parameters of the dry milling process, for  
51 the case of stainless steel 304, was considered and applied; it aims to simultaneously enhance the  
52 power factor (PF), energy consumption (EC), and surface roughness ( $R_a$ ). In addition, it was  
53 well-recognized that the effects of machining process parameters as the inputs for the  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 optimization may contribute to the variations of the measured performances of the machining  
4 operation. Therefore, an effective approach for modeling dry milling behavior and optimizing  
5 the processing factors in terms of improving working performances is still a significant  
6 contribution.  
7  
8  
9  
10  
11

12 The rest of the paper is organized as follows. Section 2 presents the methods used for the  
13 proposed optimization problems. Section 3 presents the experimental setting and measurements.  
14 Section 4 presents results and discussions. Finally, summaries and conclusions are presented in  
15 Section 5.  
16  
17  
18  
19  
20

## 21 **2. Methods**

### 22 **2.1 Optimizing issue**

23  
24  
25 The power factor (PF) is defined as the ratio of the active power consumption (APC) to  
26 the apparent power (APP), as shown in Eq. 1.  
27  
28  
29  
30  
31

$$32 \quad PF = \frac{APC}{APP} = \frac{APC}{\sqrt{APC^2 + RP^2}} \quad (1)$$

33  
34  
35  
36

37 The power transmitted from the electrical source to the device contains two sub-  
38 components, including the active power and reactive power (RP). The active power characterizes  
39 the useful capacity of the device. Reactive power does not produce any productive work but it is  
40 necessary for energy transformation. Reactive power significantly creates a magnetic field for  
41 transferring electrical energy into other forms of energy. The apparent power is the vector sum of  
42 the active power and reactive power. The higher the power factor, the higher the active power  
43 and the device will produce more useful power. In fact, the power factor depends on a load of  
44 electrical equipment<sup>31</sup>. For a milling machine, most of the sub-systems have a variable speed and  
45 variable operating load, which leads to the changes in the power factor. The variations of  
46 machining conditions, such as the cutting speed, feed, depth of cut, nose radius, lubrication  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60



1  
2  
3 conditions, and workpiece materials, may cause the variable loads; hence the power factor  
4 changes. Therefore, when considering the power consumption of a machining process, the  
5 selection of relevant machining conditions to enhance the power factor is always necessary and  
6 important.  
7  
8  
9  
10  
11

12 The average value of the power factor is calculated at the fifteen positions over the  
13 cutting time. Here, PF is computed using Eq. 2.

$$PF = \frac{1}{n} \sum_{i=1}^n PF_i \quad (2)$$

14 where  $PF_i$  and  $n$  are the power factor at the  $i$  position and the total measured point, respectively.

15  
16  
17  
18  
19  
20  
21  
22 Figure 1 presents a typical total energy consumed in a machine tool that can be divided  
23 into four components, including the setting energy, air cutting energy, cutting energy, and tool  
24 changing energy. Practically, the energy consumed for setting, air cutting, and tool changing  
25 times can be considered as constant values due to their less dependence on processing conditions  
26 (machining process parameters: cutting speed, depth of cut, feed rate, and nose radius).  
27 Therefore, the energetic objective in this work focuses on energy consumption in the cutting  
28 stage which is effectively used to remove the material from the workpiece. In this study, the  
29 energy consumption (EC) in cutting time is calculated using Eq. 3:  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40

$$EC = P_c \times t_c \quad (3)$$

41 where  $P_c$  and  $t_c$  denote the power consumed and the cutting time, respectively.

42  
43  
44  
45  
46 Table 1 presents the processing inputs, including the cutting speed ( $V$ ), depth of cut ( $a$ ),  
47 feed rate ( $f$ ), and nose radius ( $r$ ) for a multi-response optimization, which aims to enhance  
48 simultaneously the power factor and decrease the energy consumption and surface roughness in  
49 the dry machining. The levels of the processing inputs are determined based on the common  
50 values used in the milling processes of the automotive components and verified by cutting tool's  
51 handbooks.  
52  
53  
54  
55  
56  
57  
58  
59  
60

## 2.2 Optimizing framework

The systematic optimization procedure is shown in Fig. 2, including 5 sequential steps presented as follows:

Step 1: The machining runs are conducted according to the experimental matrix generated by the Box-Behnken method (BBM) <sup>32</sup>. BBM is chosen due to an acceptable balance between predictive accuracy and economy. The Box-Behnken method is an effective method, which combines a two-level factorial design. Three required levels of each factor are “1”, “0”, and “+1”, which present the low, middle and high levels. The number of design points is placed on the midpoints of the edges and the center of the block. BBM is more efficient than the other techniques, such as central composite and full factorial designs due to a lower number of experiments, which significantly contribute to experimental costs and time. The full factorial designs are costly in terms of real-machining experiments when the factor number is higher than 2. Moreover, BBM does not present the parameter combinations at their highest or lowest levels. The experiments are avoided to perform at extreme conditions, which may lead to unsatisfactory results.

Step 2: The PF, EC, and  $R_a$  models are then developed with respect to process parameters using the RBF approximate approach.

Step 3: Normalization of the experimental data using the GRA <sup>33</sup>.

The normalized value for the response with the “smaller-the-better” characteristic is calculated using Eq. 4.

$$x_i^*(k) = \frac{\max x_i(k) - x_i(k)}{\max x_i(k) - \min x_i(k)} \quad (4)$$

The normalized value for the response with the “higher-the-better” characteristic is computed with the help of Eq. 5.

$$x_i^*(k) = \frac{x_i(k) - \min x_i(k)}{\max x_i(k) - \min x_i(k)} \quad (5)$$

where  $x_i(k)$  denotes the actual value. Additionally,  $\max x_i(k)$  and  $\min x_i(k)$  are the maximum and minimum values of the response, respectively.

The deviation sequence  $\Delta_i(k)$  is calculated by applying Eq. 6.

$$\Delta_i(k) = |x_0^*(k) - x_i^*(k)| \quad (6)$$

The value of the grey relation coefficients  $\xi_i(k)$  for each response is calculated according to Eq. 7.

$$\xi_i(k) = \frac{\Delta_{\min} + \zeta * \Delta_{\max}}{\Delta_i(k) + \zeta * \Delta_{\max}} \quad (7)$$

where  $\Delta_{\max}$  and  $\Delta_{\min}$  are the maximum and minimum values of  $\Delta_i(k)$ , respectively.  $\zeta$  denotes the distinguishing factor.

Step 4: Determining the weight values of performances using the principal component analysis (PCA).

The correlation coefficient from the grey relation coefficient is calculated using Eq. 8.

$$R_{jl} = \left[ \frac{\text{Cov}(x_i(j), x_i(l))}{\sigma x_i(j) * \sigma x_i(l)} \right], j = 1, 2, \dots, m, l = 1, 2, \dots, n. \quad (8)$$

where  $x_i(j)$  and  $\text{cov}(x_i(j), x_i(l))$  are the grey relational coefficient and the covariance of the response, respectively. Additionally,  $\sigma x_i(j)$  and  $\sigma x_i(l)$  are the standard deviations of the response, respectively. The eigenvalues and consequent eigenvectors are determined by applying Eq. 9.

$$(R - \lambda_k I_m) V_{ik} = 0 \quad (9)$$

where  $\lambda_k$ ,  $V_{ik}$ , and  $I_m$  represent the eigenvalue, the eigenvector, and the identity matrix, respectively. Therefore, the principal component is obtained using Eq. 10.

$$Y_{mk} = \sum_{i=1}^n x_m(i) V_{ik} \quad (10)$$

where  $x_m(i)$  and  $Y_{mk}$  are the normalized response variable and the principal component, respectively.

Step 5: Determining the optimal parameters using the desirability approach (DA).

The DA is applied to transform the response  $y_i(x)$  into an individual desirability function  $d_i$  ( $0 \leq d_i \leq 1$ ) for achieving the desired value. The value of  $d_i$  lies between 0 and 1, when  $d_i = '1'$ . It indicates that the ideal response is achieved. The optimal results of the response are adjusted with different weight values. The targets are combined into the desirability function ( $D$ ) for multi-objective and processing factors. The optimal factors are determined based on the maximum value of the desirability function.

The  $d_i$  is calculated with respect to the maximizing goal, as shown in Eq. 11.

$$d_i = \begin{cases} 0, Y_i \leq L_i \\ \left( \frac{Y_i - L_i}{H_i - L_i} \right)^w, L_i < Y_i < H_i \\ 1, Y_i \geq H_i \end{cases} \quad (11)$$

The  $d_i$  is calculated with respect to the minimizing goal, as shown in Eq. 12.

$$d_i = \begin{cases} 0, Y_i \leq L_i \\ \left( \frac{H_i - Y_i}{H_i - L_i} \right)^w, L_i < Y_i < H_i \\ 1, Y_i \geq H_i \end{cases} \quad (12)$$

The  $d_i$  is calculated with respect to the target, as shown in Eq. 13.

$$d_i = \begin{cases} \left( \frac{Y_i - L_i}{T_i - L_i} \right)^{w1}, L_i < Y_i < T_i \\ \left( \frac{Y_i - H_i}{T_i - H_i} \right)^{w2}, T_i < Y_i < H_i \\ 0, otherwise \end{cases} \quad (13)$$

The  $d_i$  is calculated with respect to the range, as shown in Eq. 14.

$$d_i = \begin{cases} 1, L_i < Y_i < H_i \\ 0, otherwise \end{cases} \quad (14)$$

where  $L_i$ ,  $H_i$ ,  $T_i$ , and  $w_i$  are the low, high, target, and weight values of the  $i_{th}$  response, respectively.

The value of the desirability function of the response is calculated by means of Eq. 15.

$$D = \left( \frac{N}{\prod_{i=1}^N d_i^{r_i}} \right)^{1/\sum r_i} \quad (15)$$

where  $N$  is the number of the measured responses.

### 2.3 Radial Basis Function model

RBF (radial basis function) is one kind of neural networks using a hidden layer of radial units and an output layer of linear units, which is applied to interpolate the data points. RBF approximations are characterized by the reasonably fast training and compact networks. They are useful in approximating a wide range of nonlinear spaces. The RBF is expressed as a formula in Eq. 16<sup>34</sup>.

$$F(x) = \sum_{i=1}^n \lambda_i \phi((x - x_i) + bx + C) \quad (16)$$

where  $\gamma$  is a positive constant.  $\lambda_i$ ,  $b$ , and  $c$  are the parameters to be determined, respectively, which are obtained by Eq. 17 & 18 in the matrix form.

$$\begin{bmatrix} \phi & P \\ P^T & 0 \end{bmatrix} \begin{Bmatrix} \lambda \\ a \end{Bmatrix} = \begin{Bmatrix} F \\ 0 \end{Bmatrix} \quad (17)$$

$$P = \begin{Bmatrix} 1 & X_1^T \\ 1 & X_2^T \\ \cdot & \cdot \\ \cdot & \cdot \\ \cdot & \cdot \\ 1 & X_n^T \end{Bmatrix}, \lambda = \begin{Bmatrix} \lambda_1 \\ \lambda_2 \\ \cdot \\ \cdot \\ \cdot \\ \lambda_n \end{Bmatrix}, a = \begin{Bmatrix} c \\ b_2 \\ \cdot \\ \cdot \\ \cdot \\ b_d \end{Bmatrix}, b = \begin{Bmatrix} b_1 \\ b_2 \\ \cdot \\ \cdot \\ \cdot \\ b_d \end{Bmatrix}, F = \begin{Bmatrix} f(x_1) \\ f(x_2) \\ \cdot \\ \cdot \\ \cdot \\ f(x_2) \end{Bmatrix} \quad (18)$$

where  $\phi$  and  $d$  are the  $n \times n$  matrix and the dimension of vector  $\mathbf{X}$ , respectively.

In this study, the multi-quadratic models of the radius basic function are used to render the nonlinear approximations, which are presented using Eq. 19.

$$\phi(r) = \sqrt{r^2 + \gamma^2} \quad (19)$$

Four evaluating criteria, including the  $R^2$  value, the root mean square error (RMSE), the max absolute error (MAE), and the average absolute error (AAE) are used to investigate the predictive accuracy of the RBF models.

**R-squared ( $R^2$ )** presents the coefficient of determination, between 0 and 1 where  $R^2 = 1$  means no error between the observed an approximated values. The  $R^2$  coefficient is defined as

the ratio of explained variation to total variation. R-squared is a statistical measure of the degree of fit. The value of  $R^2$  is computed as follows:

$$R^2 = 1 - \frac{\sum_i (y_i - \hat{y}_i)^2}{\sum_i (y_i - \bar{y}_i)^2} \quad (20)$$

where  $n$ ,  $y_i$ ,  $\bar{y}_i$  and  $\hat{y}_i$  are the number of test points, the observed value, the mean of observed value, and the approximated value, respectively.

The root mean square error (RSME) is a quadratic scoring rule, which is used to measure the average magnitude of the error. In other words, it's the square root of the average of squared differences between prediction and actual observation. The value of RSME is calculated as follows:

$$RMSE = \sqrt{\frac{\sum_{i=1}^n (y_i - \hat{y}_i)^2}{n}} \quad (22)$$

The maximum absolute error (MAE) denotes the maximum difference between observed and approximated values. The value of MAE is computed as follows:

$$MAE = \max |y_i - \hat{y}_i| \quad (22)$$

The average absolute error (AAE) presents the average difference between observed and approximated values. The value of AAE is calculated as follows:

$$AAE = \frac{\sum_{i=1}^n |y_i - \hat{y}_i|}{n} \quad (23)$$

### 3. Experimental setting and measurements

Milling tests were performed in a Spinner U620 machining center (Fig. 3a). The dimensions of machining specimens were 350 mm×150 mm×25 mm. The tool holder equipped with two inserts is 12 mm in diameters. The different wiper inserts having 0.2 mm, 0.4 mm, and 0.8 mm of the nose radius are used in the milling trials.

1  
2  
3 Power Meter KEW6305 was used to measure the power consumption during the milling  
4 process. Three clamp sensors were connected to the three-phase power lines of CNC machine  
5 with correct direction. The observed data was stored on a flashcard and analyzed with the aid of  
6 the KEW6305 software on the computer, as shown in Fig. 3b.  
7  
8  
9  
10

11  
12 The surface roughness was measured using a tester Mitutoyo SJ-301 in the vertical and  
13 horizontal directions. The average values of the roughness properties were observed from five  
14 different points (Fig. 3c).  
15  
16  
17  
18

19 The representative values of the active power consumed at different inputs are depicted  
20 in Fig. 4. The profiles of the surface roughness are shown in Fig. 5. The variations of the power  
21 factor in the processing time are illustrated in Fig. 6.  
22  
23  
24  
25

## 26 **4. Results and discussion**

### 27 **4.1. Investigation of model accuracy**

28  
29 The experimental results of the dry milling process are given in Table 2.  
30  
31

32 The values of the  $R^2$ , RMSE, MAE, and AAE for three technical responses are listed in  
33 Table 3. The  $R^2$ -values of the PF, EC, and  $R_a$  are 0.9954, 0.9921, and 0.9938, respectively,  
34 showing the perfect correlation between predicted values and observed values (Fig. 7). This  $R^2$   
35 value is comparable with other established models, reported by <sup>35-37</sup>, warranting the acceptance  
36 of the present model. The small values of the evaluating errors (RMSE, MAE, and AAE)  
37 indicate the adequacy of the proposed models.  
38  
39  
40  
41  
42  
43  
44  
45  
46

47 In this study, the experimental data from 1 to 25 are used to develop the RBF models.  
48 The experimental data from 26 to 29 are adopted to test the accuracy of the obtained models. The  
49 comparisons between experimental and predictive values at the random points are shown in Fig.  
50 8. The small errors indicate that the RBF models are adequate and can be used for the optimizing  
51 process.  
52  
53  
54  
55  
56  
57  
58  
59  
60

## 4.2. Parametric effects

The effects of the inputs on the power factor shown in Fig. 9 pointed out that the higher levels of the processing inputs, including the cutting speed, depth of cut, feed rate, and nose radius lead to a higher power factor. Fig. 9a exhibits the impacts of the cutting speed and nose radius on the power factor. At a higher value of the cutting speed, the consumed power of the motor increases in order to reach the desired value of the spindle speed. Therefore, the active power increases, leading to a higher power factor. As nose radius increases, the cutting edge becomes curved, which results in more material deformation at the cutting area and thus higher energy consumption. Moreover, a larger radius increases the length of the cutting edge; hence, more power is consumed to overcome the frictional resistance. Therefore, a higher nose radius leads to an increased load on the motor; hence, the power factor improves.

The influences of the feed rate and depth of cut on the power factor are displayed in Fig. 9b. When the feed and depth of cut increases, the undeformed chip section increases. This results in higher machining forces<sup>38, 39</sup>; hence the machine tool consumes more power. In fact, an increment in the depth of cut or feed rate causes an increased load on the motor to remove a higher material volume. As a result, higher active power is observed, resulting in an increment in the power factor.

Fig. 9c shows that  $f$  is the most effective parameter on the power factor due to the highest contribution regarding single term (22.81 %), followed by  $a$  (16.33 %),  $V$  (14.98 %), and  $r$  (10.64 %), respectively. When the feed rate increases, the cutting forces and the cutting momentum also increase. Hence, the active power of the servo spindle motor and the feed drive motors increases. As a result, the PF rises up. The feed rate has more effect on the PF than that of cutting speed due to the contribution of the active power of the feed drive motors. When the feed rate increases, the reaction forces on the X and Y-axis of the feed drive system as well as the cutting momentum on the spindle motor increase. Therefore, the total active power of



1  
2  
3 movement system increase. The significant quadratic terms have significant impacts, in which  $r^2$   
4 has the largest contribution (8.42 %); followed by  $f^2$  (6.31 %),  $V^2$  (5.77 %) and  $a^2$  (2.68 %),  
5  
6  
7 respectively.  
8

9  
10 The interaction impacts of the processing conditions on energy consumption are shown in  
11 Fig. 10. Fig. 10a depicts the impacts of the cutting speed and depth of cut on energy  
12 consumption. An increment in the depth of cut increases the undeformed chip section and the  
13 degree of plastic deformation <sup>40</sup>. The greater resistance in the chip formation increases and  
14 higher energy is consumed. As the cutting speed increases, energy consumption significantly  
15 decreases. An increased cutting speed causes an increment in the temperature of the cutting  
16 region; hence, the hardness and strength of the workpiece are decreased. The softened part of  
17 material causes lower machining forces, as compared to its harder state. Additionally, an  
18 increased cutting speed leads to a decrease in the frictional coefficient and the lower cutting  
19 force is obtained. Therefore, higher cutting speed generates low cutting forces which result in  
20 less energy consumption. In contrast, it is obvious that the material removal rate would be higher  
21 when the cutting speed increased. The process parameters, including the cutting speed, feed, and  
22 depth of cut determine the material removal rate. An increment in the material removal rate  
23 requires higher power consumption. Higher rate of material removal required a higher power to  
24 turn the spindle motor.  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43

44 The impacts of the feed rate and nose radius on energy consumption are shown in Fig. 10b.  
45 Higher feed rate causes a rise in heat generated on the workpiece surface and tool and may lead  
46 to the formation of build-up-edge (BUE). The BUE can increase the cutting forces due to an  
47 increment in the contact area between the cutting tool and workpiece, resulting in higher power  
48 consumed. Additionally, the BUE causes an increase in the cutting tool temperature, which leads  
49 to an increase in the mechanical strength of the chip due to the work-hardening behavior.  
50 Obviously, higher power consumed is required to detach material. Fortunately, a higher value of  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 the feed rate or cutting speed leads to a decrease in the cutting time, resulting in a reduction in  
4 the energy consumed. Reduction in energy consumption with an increase in feed rate and/or  
5 cutting speed is logical because it results in faster machining and less processing time <sup>41</sup>. It is  
6 inferred from Fig. 10b that an increased radius leads to an increment in cutting edge; hence, the  
7 cutting tool becomes blunt. The degree of the material deformation increases and more energy is  
8 required to overcome the resistance friction <sup>42</sup>.  
9

10  
11  
12 In Fig. 10c, it is found that  $f$  is the most effective parameter on energy consumption due to  
13 the highest contribution regarding single term (29.78 %), followed by  $V$  (19.55 %),  $a$  (5.00 %),  
14 and  $r$  (2.92 %), respectively. It is observed that energy consumption for the milling process is  
15 highly sensitive to feed rate as compared to the cutting speed due to the greater impact of the  
16 feed drive motors. As the feed rate increases, the load of the motor on the feed drive systems  
17 increases to reach the desired value and higher reaction forces are required. Therefore, the power  
18 used of movement system increases. The term  $f^2$  has the largest contribution with respect to the  
19 quadratic terms (15.46 %), followed by  $V^2$  (9.07 %),  $r^2$  (1.11 %) and  $a^2$  (0.43 %), respectively.  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34

35 Fig. 11 depicted the influences of machining parameters on the surface roughness. The  
36 influences of the cutting speed and nose radius on the surface roughness are shown in Fig. 11a.  
37 An increment in the cutting speed leads to a decrease in the strength and hardness of the  
38 workpiece due to an increase in the temperature of the cutting region. The chip produced is  
39 easily detached from the workpiece, resulting in a reduction in surface roughness. Additionally,  
40 higher cutting speed reduces cutting forces together with the effect of natural frequency and  
41 vibration, giving a better surface finish. Moreover, the possibility of the formation of the BUE at  
42 high cutting speed is comparatively lower and thus generates smoother surfaces. An increased  
43 radius results in an increment in contact length between the milled surface and tool radius,  
44 leading to smaller peaks on the trail. The roughness profile is decreased with a high tip radius,  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 resulting in a smoother surface. Additionally, the chatter could be suppressed due to an  
4  
5 increment in stand damping with an increased radius <sup>43</sup>.  
6

7  
8 Fig. 11b shows that an increased roughness is associated with the increased feed rate  
9  
10 and/or depth of cut. At a low value of the feed rate, the distance between the peak and crest of  
11  
12 the machined surface is short; hence, a smoother surface is produced. An increase in the feed rate  
13  
14 causes higher distance between the peaks generated by the tool grooves left on the milled  
15  
16 surface. Therefore, roughness values increase with feed rate due to more feed marks on the  
17  
18 machined surface. At a higher value of the feed rate, the BUE can result in grooves formation  
19  
20 and increases the degree of the plastic deformation. The machining parts of the workpiece are  
21  
22 heavily detached from the surface, leading to a worsening surface <sup>44</sup>. As the depth of cut  
23  
24 increases, the contact area between the workpiece and the cutting tool increases, resulting in an  
25  
26 increment in the material removal volume and cutting forces. It is also possible that the  
27  
28 increment in the cutting forces, due to the increase of depth of cut above the stability lobe,  
29  
30 caused chatter in machine tool which eventually resulted in poor surface finish i.e. an increase in  
31  
32 surface roughness <sup>45</sup>. Low depth of cut should be used to decrease the tendency of chatter.  
33  
34  
35  
36

37  
38 Fig. 11c shows the effects of machining parameters on the surface roughness. As a result,  
39  
40 the percentage contributions of the  $f$ ,  $r$ ,  $a$ , and  $V$  are 17.37 %, 16.26 %, 16.11 %, and 13.91 %,  
41  
42 respectively. All quadratic factors have significant effects, in which  $f^2$  is the most influenced  
43  
44 factor (14.36 %), followed by  $V^2$  (3.69 %),  $r^2$  (2.79 %) and  $a^2$  (2.54 %), respectively.  
45  
46

47  
48 The effects of different processing factors on the machined surface morphology are  
49  
50 exhibited in Fig. 12. The machined defects such as pits, voids, and grooves are appeared at low  
51  
52 cutting speed, as depicted in Fig. 12a. The smooth cut and small waviness, as well as grooves,  
53  
54 are observed at a higher value of the cutting speed (Fig. 12b). The surface faults, including  
55  
56 cracks, grooves, and valleys are displayed at the highest feed rate (Fig. 12d), as compared to the  
57  
58 lowest one (Fig. 12c).  
59  
60

1  
2  
3 The wear behaviors of the inserts at various machining conditions are shown in Fig. 13. As  
4 depicted in Fig. 13a, the wear pattern is not much prominent, no groove or skin depletion.  
5  
6 However, when the feed rate was increased, the wear pattern shows crater wear on the rake face,  
7 associated with edge chipped off – the fracture of cutting edge. To support this, it can be seen  
8 from Table 2, the power factor is increased from 0.566 to 0.752 (32% increase), and the resulted  
9 surface roughness increased from 0.98 to 1.55 (58% increase). An increased input leads to a  
10 higher temperature at the nose region, which causes excessive pressure and stress. The  
11 deformation of the cutting edge is increased with an increment in the factor, leading to the  
12 reduction of the hardness of the tool.  
13  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23

### 24 **4.3. Optimal results**

25  
26 The pre-processing and corresponding values for two objectives after a linear  
27 normalization are listed in Table 4. The values of the GRC are shown in Table 5. As depicted in  
28 Table 6, the percentage contribution of the first principal component is 52.00 %, followed by the  
29 second component (33.20 %) and the third one (14.70 %), respectively. The weight values are  
30 calculated based on the squares of subsequent eigenvectors of the three principal components.  
31 Table 7 revealed that the weight values of the power factor (PF), energy consumption (EC), and  
32 surface roughness ( $R_a$ ) using the principal component analysis (PCA) method are 0.32, 0.35, and  
33 0.33, respectively.  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44

45 The mathematical formulas showing the relationship between inputs and outputs are used  
46 to find optimal parameters with the support of the DA. A total of 29 optimal results are observed  
47 and the point with the D values close to 1 is the best solution. The optimal values of the inputs  
48 are shown in Fig. 14a. The values of the desirability are depicted in Fig. 14b. The desirability of  
49 0.97515 revealed that the optimal results observed are reliable and feasible. As revealed in Table  
50 8, the reduction of the EC and  $R_a$  are about 34.85 % and 57.65 %, respectively, while the PF  
51 increases around 28.83 %, as compared to the initial values.  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 To evaluate the effectiveness of the proposed approach, a confirmatory experiment is  
4 conducted at the optimal solution. The experimental results are exhibited in Fig. 15. The  
5 comparative results are shown in Table 9. The small errors (below 5 %) indicate that optimal  
6 results are strongly correlated with the experimental data. The similar ranges for the predictive  
7 errors can be found in the works of <sup>46, 47</sup>. Therefore, the developed approach can be effectively  
8 applied to the optimization of different milling processes.  
9

10  
11  
12 As mentioned in the previous section, wet machining with liquid coolants is normally used  
13 in metal-machining operations and processes to reduce the temperature of both workpiece and  
14 tool and to evacuate chips from the cutting area. However, the heavy use of coolant fluids is not  
15 cost-effective and causes poor environmental impacts, especially there are more and more  
16 concerns regarding safety and environmental legislations applied in manufacturing industries,  
17 with emerging trends towards sustainable manufacturing. Today, dry machining is considered as  
18 one of the eco-friendly machining processes, with good environmental impacts and cost-  
19 effectiveness. Dry machining is becoming more prevalent, and it also helps to increase tool life  
20 when machining the steels, cast iron, and some stainless materials. There have been emerging  
21 needs and growing efforts to investigate optimal machining process parameters for the dry  
22 machining operations. This study focuses on the optimization of the machining process  
23 parameters, aimed to enhance simultaneously the power factor, energy consumption, and surface  
24 roughness. A study did take into account not only the technical issues related to the machining  
25 process quality (surface roughness) but also environmental impacts and sustainable  
26 manufacturing ones: maximizing the power factor and decreasing the energy consumption. A  
27 specific case study of dry machining of stainless steel 304 was successfully implemented to  
28 investigate optimizations of the machining process parameters and cutting tool's geometry for  
29 simultaneous improvements of the power factor (PF), energy consumption (EC), and surface  
30 roughness (Ra). The outcomes and findings of the investigated work in this study can be used for  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 further research in sustainable design and manufacturing as well as directly used in the  
4 knowledge-based and expert systems for dry milling applications in industrial practices.  
5  
6

## 7 **5. Conclusions**

8  
9  
10 This paper presents a multi-response optimization which aims to simultaneously enhance  
11 the power factor (PF), decrease the energy consumption (EC), and improve the machining  
12 quality via reduction of the surface roughness ( $R_a$ ), for the specific case of dry machining of  
13 stainless steel 304. The radial basis function (RBF) models of three technical responses were  
14 developed in terms of the machining process parameters, including the cutting velocity ( $V$ ), feed  
15 rate ( $f$ ), depth of cut ( $a$ ), and tool nose radius ( $r$ ). An integrative approach, including the grey  
16 relation analysis (GRA), the principal component analysis (PCA), and desirability approach  
17 (DA) was used to calculate the weight objectives and predict the optimal values of machining  
18 process parameters (cutting velocity, feed rate, depth of cut, and tool nose radius). The key  
19 conclusions of this study can be presented as follows:  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32

33 1. The RBF models for the power factor (PF), energy consumption (EC), and surface  
34 roughness ( $R_a$ ), have  $R^2$ -values of 0.9954, 0.9921, and 0.9938, respectively. This indicates a  
35 good agreement between the predicted and experimental values. The proposed optimization  
36 models adequately exhibit the nonlinear relationships among process parameters and machining  
37 responses or technical outputs (power factor, energy consumption, and surface roughness). The  
38 developed correlations can be used to predict the optimal machining process parameters with a  
39 sufficient accuracy when dry-machining of stainless steel 304.  
40  
41  
42  
43  
44  
45  
46  
47  
48

49 2. It can be concluded that the processing conditions, including the cutting speed ( $V$ ), depth  
50 of cut ( $a$ ), feed rate ( $f$ ), and tool nose radius ( $r$ ), have significant impacts on the technical outputs,  
51 including power factor (PF), energy consumption (EC), and surface roughness ( $R_a$ ). In order to  
52 increase the power factor, the maximal levels of the process parameters are recommended for  
53 utilization. The highest values of the cutting speed and feed rate can be used to save the energy  
54  
55  
56  
57  
58  
59  
60

1  
2  
3 consumption, while the lowest levels of the depth of cut and nose radius cause a decrease in  
4 consumed energy. The low values of the depth of cut and feed rate are recommended to decrease  
5 the surface roughness. The highest levels of the tool nose radius and cutting speed can be used to  
6 get a smoother surface.  
7  
8  
9  
10

11  
12 3. The selection of the weight of objectives could give a better solution to determine the  
13 optimal machining process parameters. The optimal values of cutting speed ( $V$ ), depth of cut ( $a$ ),  
14 feed rate ( $f$ ), and tool nose radius ( $r$ ), are 160 m/min, 0.42 mm, 0.09 mm/z, and 0.8 mm,  
15 respectively. The power factor improves about 28.83 %, and the energy consumption and surface  
16 roughness decrease approximately 34.85 % and 57.65 % at the optimal solution using the weight  
17 values generated by Principal Component Analysis (PCA).  
18  
19  
20  
21  
22  
23  
24  
25

26 4. The hybrid approach including the RBF (Radial Basis Function) models, GRA (Grey  
27 Relation Analysis), PCA (Principal Component Analysis), and DA (Desirability approach) can  
28 facilitate the optimization of the milling process; and this approach gives a reliable optimal  
29 solution, as compared to using practical experience or operation guide.  
30  
31  
32  
33  
34

35 5. Practically, the variation of the inputs (process parameters: cutting speed, depth of cut,  
36 feed rate, and tool nose radius) may lead to a conflict or contradictory impacts on the outputs  
37 (power factor, energy consumption and surface roughness) in dry-milling. In this way, a  
38 comprehensive optimization should be considered with more objectives, such as surface  
39 properties, tool life, and machining productivity.  
40  
41  
42  
43  
44  
45  
46  
47  
48

#### 49 **ACKNOWLEDGMENT**

50  
51 This research is funded by Vietnam National Foundation for Science and Technology  
52 Development (NAFOSTED) under grant number 107.04-2017.06  
53

54 This work was also supported by a Researcher Links workshop grant, 2017-RLWK9-11081,  
55 under the Newton Fund Vietnam Programme partnership. The grant is funded by the UK  
56  
57  
58  
59  
60

1  
2  
3 Department of Business, Energy and Industrial Strategy (BEIS) and delivered by the British  
4 Council. For further information, please visit [www.newtonfund.ac.uk](http://www.newtonfund.ac.uk).  
5  
6  
7  
8  
9

## 10 **DECLARATION OF CONFLICTING INTERESTS**

11  
12 The author(s) declared no potential conflicts of interest with respect to the research, authorship,  
13 and/or publication of this article.  
14  
15  
16  
17  
18

## 19 **REFERENCES**

- 20  
21 1. Krolczyk GM, Maruda RW, Krolczyk JB, et al. Ecological trends in machining as a key  
22 factor in sustainable production – A review. *Journal of Cleaner Production* 2019; 218: 601-615.  
23 DOI: <https://doi.org/10.1016/j.jclepro.2019.02.017>.  
24  
25  
26  
27 2. Gupta S, Dangayach G, Singh AK, et al. A pilot study of sustainable machining process  
28 design in Indian process industry. *CAD/CAM, Robotics and Factories of the Future*. Springer,  
29 2016, pp.379-385.  
30  
31  
32  
33 3. Bagaber SA and Yusoff AR. Multi-objective optimization of cutting parameters to  
34 minimize power consumption in dry turning of stainless steel 316. *Journal of Cleaner Production*  
35 2017; 157: 30-46.  
36  
37  
38  
39 4. Danish M, Ginta TL, Habib K, et al. Thermal analysis during turning of AZ31  
40 magnesium alloy under dry and cryogenic conditions. *The International Journal of Advanced*  
41 *Manufacturing Technology* 2017; 91: 2855-2868.  
42  
43  
44  
45 5. Mia M and Dhar NR. Modeling of Surface Roughness Using RSM, FL and SA in Dry  
46 Hard Turning. *Arabian Journal for Science and Engineering* 2018; 43: 1125-1136. DOI:  
47 [10.1007/s13369-017-2754-1](https://doi.org/10.1007/s13369-017-2754-1).  
48  
49  
50  
51 6. Bhopale NN, Pawade RS and Joshi SS. Surface quality analysis in ball end milling of  
52 Inconel 718 cantilevers by response surface methodology. *Proceedings of the Institution of*  
53 *Mechanical Engineers, Part B: Journal of Engineering Manufacture* 2017; 231: 628-640.  
54  
55  
56  
57  
58  
59  
60



- 1  
2  
3 7. Chen H-Q and Wang Q-H. Modelling and simulation of surface topography machined by  
4 peripheral milling considering tool radial runout and axial drift. Proceedings of the Institution of  
5 Mechanical Engineers, Part B: Journal of Engineering Manufacture 2019: 0954405419838384.  
6  
7
- 8 8. Babu GP, Murthy B, Venkatarao K, et al. Multi-response optimization in orthogonal turn  
9 milling by analyzing tool vibration and surface roughness using response surface methodology.  
10 Proceedings of the Institution of Mechanical Engineers, Part B: Journal of Engineering  
11 Manufacture 2017; 231: 2084-2093.  
12  
13
- 14 9. Le Coz G and Dudzinski D. Temperature variation in the workpiece and in the cutting  
15 tool when dry milling Inconel 718. The International Journal of Advanced Manufacturing  
16 Technology 2014; 74: 1133-1139.  
17  
18
- 19 10. Jomaa W, Lévesque J, Bocher P, et al. Optimization study of dry peripheral milling  
20 process for improving aeronautical part integrity using Grey relational analysis. The  
21 International Journal of Advanced Manufacturing Technology 2017; 91: 931-942.  
22  
23
- 24 11. Khettabi R, Nouioua M, Djebara A, et al. Effect of MQL and dry processes on the  
25 particle emission and part quality during milling of aluminum alloys. The International Journal  
26 of Advanced Manufacturing Technology 2017; 92: 2593-2598.  
27  
28
- 29 12. Safari H, Sharif S, Izman S, et al. Surface integrity characterization in high-speed dry end  
30 milling of Ti-6Al-4V titanium alloy. The International Journal of Advanced Manufacturing  
31 Technology 2015; 78: 651-657.  
32  
33
- 34 13. Shihab SK, Khan ZA, Mohammad A, et al. Optimization of surface integrity in dry hard  
35 turning using RSM. Sadhana 2014; 39: 1035-1053.  
36  
37
- 38 14. Angappan P, Thangiah S and Subbarayan S. Taguchi-based grey relational analysis for  
39 modeling and optimizing machining parameters through dry turning of Incoloy 800H. Journal of  
40 Mechanical Science and Technology 2017; 31: 4159-4165.  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

- 1  
2  
3 15. Krolczyk G, Nieslony P and Legutko S. Determination of tool life and research wear  
4 during duplex stainless steel turning. Archives of Civil and Mechanical Engineering 2015; 15:  
5 347-354.  
6  
7  
8  
9  
10 16. Baowan P, Saikaew C and Wisitsoraat A. Influence of helix angle on tool performances  
11 of TiAlN-and DLC-coated carbide end mills for dry side milling of stainless steel. The  
12 International Journal of Advanced Manufacturing Technology 2017; 90: 3085-3097.  
13  
14  
15 17. Pham T-H, Nguyen D-T, Banh T-L, et al. Experimental study on the chip morphology,  
16 tool–chip contact length, workpiece vibration, and surface roughness during high-speed face  
17 milling of A6061 aluminum alloy. Proceedings of the Institution of Mechanical Engineers, Part  
18 B: Journal of Engineering Manufacture 2019: 0954405419863221.  
19  
20  
21 18. Jahan MP, Ma J, Hanson C, et al. Tool wear and resulting surface finish during micro slot  
22 milling of polycarbonates using uncoated and coated carbide tools. Proceedings of the Institution  
23 of Mechanical Engineers, Part B: Journal of Engineering Manufacture 2019:  
24 0954405419862479.  
25  
26  
27 19. Mia M and Dhar NR. Influence of single and dual cryogenic jets on machinability  
28 characteristics in turning of Ti-6Al-4V. Proceedings of the Institution of Mechanical Engineers,  
29 Part B: Journal of Engineering Manufacture 2019; 233: 711-726. DOI:  
30 10.1177/0954405417737581.  
31  
32  
33 20. Kant G and Sangwan KS. Prediction and optimization of machining parameters for  
34 minimizing power consumption and surface roughness in machining. Journal of Cleaner  
35 Production 2014; 83: 151-164. DOI: <https://doi.org/10.1016/j.jclepro.2014.07.073>.  
36  
37  
38 21. Mia M, Królczyk G, Maruda R, et al. Intelligent Optimization of Hard-Turning  
39 Parameters Using Evolutionary Algorithms for Smart Manufacturing. Materials 2019; 12: 879.  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

22. Zhang C, Zhou Z, Tian G, et al. Energy consumption modeling and prediction of the milling process: a multistage perspective. *Proceedings of the Institution of Mechanical Engineers, Part B: Journal of Engineering Manufacture* 2018; 232: 1973-1985.
23. Nur R, Noordin M, Izman S, et al. Machining parameters effect in dry turning of AISI 316L stainless steel using coated carbide tools. *Proceedings of the Institution of Mechanical Engineers, Part E: Journal of Process Mechanical Engineering* 2017; 231: 676-683.
24. Bagaber SA and Yusoff AR. Energy and cost integration for multi-objective optimisation in a sustainable turning process. *Measurement* 2019; 136: 795-810.
25. Zhang H, Deng Z, Fu Y, et al. A process parameters optimization method of multi-pass dry milling for high efficiency, low energy and low carbon emissions. *Journal of Cleaner Production* 2017; 148: 174-184.
26. Song Q, Liu Z, Ju G, et al. A generalized cutting force model for five-axis milling processes. *Proceedings of the Institution of Mechanical Engineers, Part B: Journal of Engineering Manufacture* 2019; 233: 3-17.
27. Kuram E. Micro-milling of unreinforced and reinforced polypropylene. *Proceedings of the Institution of Mechanical Engineers, Part B: Journal of Engineering Manufacture* 2019; 233: 87-98.
28. Yang S, He C and Zheng M. Investigation on the stress field of milling titanium alloys with micro-textured ball-end milling cutter. *Proceedings of the Institution of Mechanical Engineers, Part B: Journal of Engineering Manufacture* 2019: 0954405419831491.
29. Khorram A. Laser brazing of 321 and 410 stainless steels with AMS 4777 filler metal: Experimental and numerical study. *Proceedings of the Institution of Mechanical Engineers, Part B: Journal of Engineering Manufacture* 2019; 233: 1062-1074.
30. Balaji M, Murthy B and Rao NM. Multi response optimization of cutting parameters in drilling of AISI 304 stainless steels using response surface methodology. *Proceedings of the*

- 1  
2  
3 Institution of Mechanical Engineers, Part B: Journal of Engineering Manufacture 2018; 232:  
4  
5 151-161.  
6  
7  
8 31. Prieto J, Jones M, Barrero F, et al. Comparative analysis of discontinuous and continuous  
9  
10 PWM techniques in VSI-fed five-phase induction motor. IEEE Transactions on Industrial  
11  
12 Electronics 2011; 58: 5324-5335.  
13  
14  
15 32. Basak S, Prasad KS, Mehto A, et al. Parameter optimization and texture evolution in  
16  
17 single point incremental sheet forming process. Proceedings of the Institution of Mechanical  
18  
19 Engineers, Part B: Journal of Engineering Manufacture 2019: 0954405419846001.  
20  
21  
22 33. Lal S, Kumar S, Khan ZA, et al. Multi-response optimization of wire electrical discharge  
23  
24 machining process parameters for Al7075/Al2O3/SiC hybrid composite using Taguchi-based  
25  
26 grey relational analysis. Proceedings of the Institution of Mechanical Engineers, Part B: Journal  
27  
28 of Engineering Manufacture 2015; 229: 229-237.  
29  
30  
31 34. Hussain MF, Barton RR and Joshi SB. Metamodeling: radial basis functions, versus  
32  
33 polynomials. European Journal of Operational Research 2002; 138: 142-154.  
34  
35  
36 35. Mia M and Dhar NR. Prediction of surface roughness in hard turning under high pressure  
37  
38 coolant using Artificial Neural Network. Measurement 2016; 92: 464-474.  
39  
40  
41 36. Muthukrishnan N and Davim JP. Optimization of machining parameters of Al/SiC-MMC  
42  
43 with ANOVA and ANN analysis. Journal of Materials Processing Technology 2009; 209: 225-  
44  
45 232.  
46  
47  
48 37. Basheer AC, Dabade UA, Joshi SS, et al. Modeling of surface roughness in precision  
49  
50 machining of metal matrix composites using ANN. Journal of Materials Processing Technology  
51  
52 2008; 197: 439-444.  
53  
54  
55 38. Rahman MA, Rahman M and Kumar AS. Material perspective on the evolution of micro-  
56  
57 and nano-scale cutting of metal alloys. Journal of Micromanufacturing 2018; 1: 97-114.  
58  
59  
60

- 1  
2  
3 39. Rahman MA, Rahman M and Kumar AS. Chip perforation and 'burnishing-  
4 like' finishing of Al alloy in precision machining. Precision Engineering 2017; 50: 393-409.  
5  
6  
7 40. Rahman MA, Rahman M, Kumar AS, et al. CNC microturning: an application to  
8 miniaturization. International Journal of Machine Tools and Manufacture 2005; 45: 631-639.  
9  
10  
11 41. Bagaber SA and Yusoff AR. Multi-responses optimization in dry turning of a stainless  
12 steel as a key factor in minimum energy. The International Journal of Advanced Manufacturing  
13 Technology 2018; 96: 1109-1122.  
14  
15  
16 42. Park H-S, Nguyen T-T and Dang X-P. Multi-objective optimization of turning process of  
17 hardened material for energy efficiency. International journal of precision engineering and  
18 manufacturing 2016; 17: 1623-1631.  
19  
20  
21 43. Singh D and Venkateswara Rao P. Optimization of tool geometry and cutting parameters  
22 for hard turning. Materials and Manufacturing Processes 2007; 22: 15-21.  
23  
24  
25 44. Suresh Kumar Reddy N and Venkateswara Rao P. Performance improvement of end  
26 milling using graphite as a solid lubricant. Materials and Manufacturing Processes 2005; 20:  
27 673-686.  
28  
29  
30 45. Altintas Y and Weck M. Chatter stability of metal cutting and grinding. CIRP annals  
31 2004; 53: 619-642.  
32  
33  
34 46. Nguyen T-T. Prediction and optimization of machining energy, surface roughness, and  
35 production rate in SKD61 milling. Measurement 2019; 136: 525-544.  
36  
37  
38 47. Kumar R, Hynes NRJ, Pruncu CI, et al. Multi-objective optimization of green technology  
39 thermal drilling process using grey-fuzzy logic method. Journal of Cleaner Production 2019;  
40 236: 117711.  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

**Notation**

a	Depth of cut
f	Feed rate
r	Nose radius
AAE	Average absolute error
BBM	Box-Behnken method
BUE	Build-up-edge
CNC	Computer Numerical Control
DA	Desirability approach
DM	Dry machining
EC	Energy consumption
GRA	Grey relational analysis
GRC	Grey relation coefficient
MAE	Max absolute error
PCA	Principal component analysis
PF	Power factor
$R_a$	Surface roughness
RBF	Radial basis function
RMSE	Root mean square error
RSM	Response surface methodology
SEM	Scanning electron microscopy
V	Cutting speed

**List of Figures**

Figure 1. The profile of power consumption with respect to time indicating different cutting stages

Figure 2. Systematic diagram showing the optimizing procedure

Figure 3. Experiments and measurements: (a) Dry milling experiments (b) Power measurements (c) Measuring surface roughness

Figure 4. The power consumption at various machining conditions:

(a) Experiment no. 1 (Replication-2), (b) Experiment no. 2 (Replication-2),  
(c) Experiment no. 9 (Replication-3), (d) Experiment no. 13 (Replication-3)

Figure 5. Surface roughness at various machining conditions:

(a) Experiment no. 1 (Replication-2), (b) Experiment no. 11 (Replication-3),  
(c) Experiment no. 16 (Replication-4), (d) Experiment no. 21 (Replication-3)

Figure 6. The variations of the power factor at various machining conditions:

(a) Experiment no. 11 (Replication-3), (b) Experiment no. 20 (Replication-3),  
(c) Experiment no. 24 (Replication-2)

Figure 7. Investigation of adequacy of RBF models: (a) Power factor, (b) Energy consumption, (c) Surface roughness

Figure 8. Validation of the accuracy for RBF models: (a) PF model, (b) EC model, (c) SR model

Figure 9. The effects of machining parameters on the PF model: (a) PF versus  $V$  and  $r$ ,  
(b) PF versus  $a$  and  $f$ , (c) Parameter contributions for the PF model

Figure 10. The effects of machining parameters on the EC model: (a) EC versus  $V$  and  $a$ ,  
(b) EC versus  $r$  and  $f$ , (c) Parameter contributions for the EC model

Figure 11. Interaction effects of machining parameters on the  $R_a$  model: (a)  $R_a$  versus  $r$  and  $V$ ,  
(b)  $R_a$  versus  $f$  and  $a$ , (c) Parameter contributions on the  $R_a$  model

Figure 12. SEM of surface morphology at various conditions: (a) Experiment no. 4,  
(b) Experiment no.12, (c) Experiment no.1, (d) Experiment no. 7

1  
2  
3 Figure 13. SEM images of the worn tool's rake surface at various machining conditions: (a)  
4 Experiment no. 16, (b) Experiment no. 20  
5  
6

7 Figure 14. Optimization results generated by DA: (a) Optimal values, (b) Bar graph of the  
8 desirability  
9  
10

11 Figure 15. Experimental results at the optimal solution: (a) Power consumed, (b) Power factor,  
12  
13 (c) Surface roughness  
14  
15  
16  
17  
18  
19  
20  
21  
22  
23  
24  
25  
26  
27  
28  
29  
30  
31  
32  
33  
34  
35  
36  
37  
38  
39  
40  
41  
42  
43  
44  
45  
46  
47  
48  
49  
50  
51  
52  
53  
54  
55  
56  
57  
58  
59  
60

For Peer Review



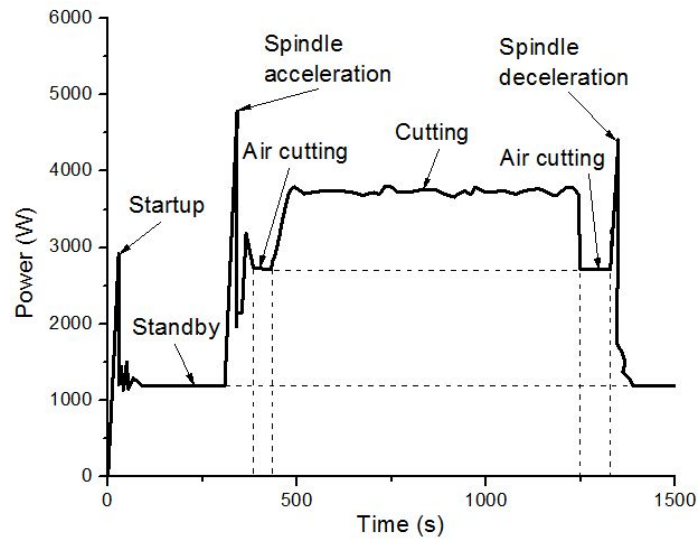


Figure 1. The profile of power consumption with respect to time indicating different cutting stages

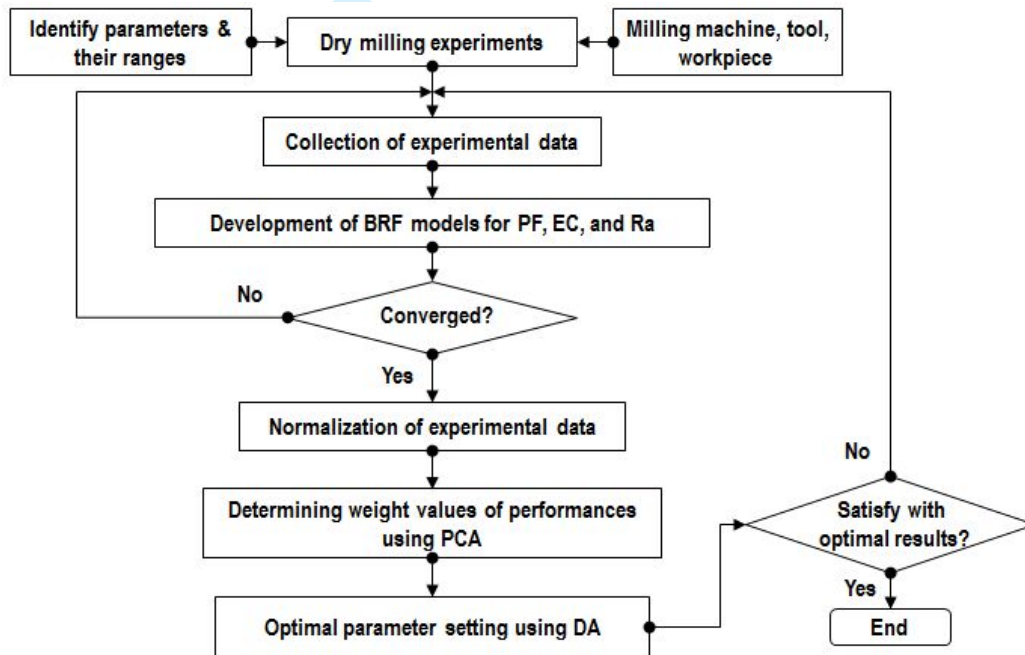


Figure 2. Systematic diagram showing the optimizing procedure

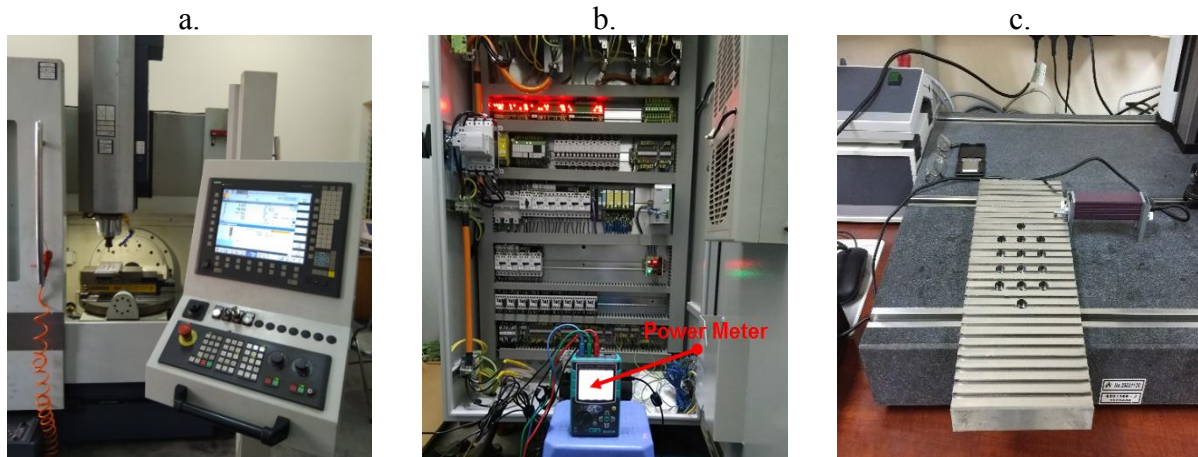


Figure 3. Experiments and measurements: (a) Dry milling experiments, (b) Power measurements, (c) Measuring surface roughness



Figure 4. The power consumption at various machining conditions:  
 (a) Experiment no. 1 (Replication-2), (b) Experiment no. 2 (Replication-2),  
 (c) Experiment no. 9 (Replication-3), (d) Experiment no. 13 (Replication-3)

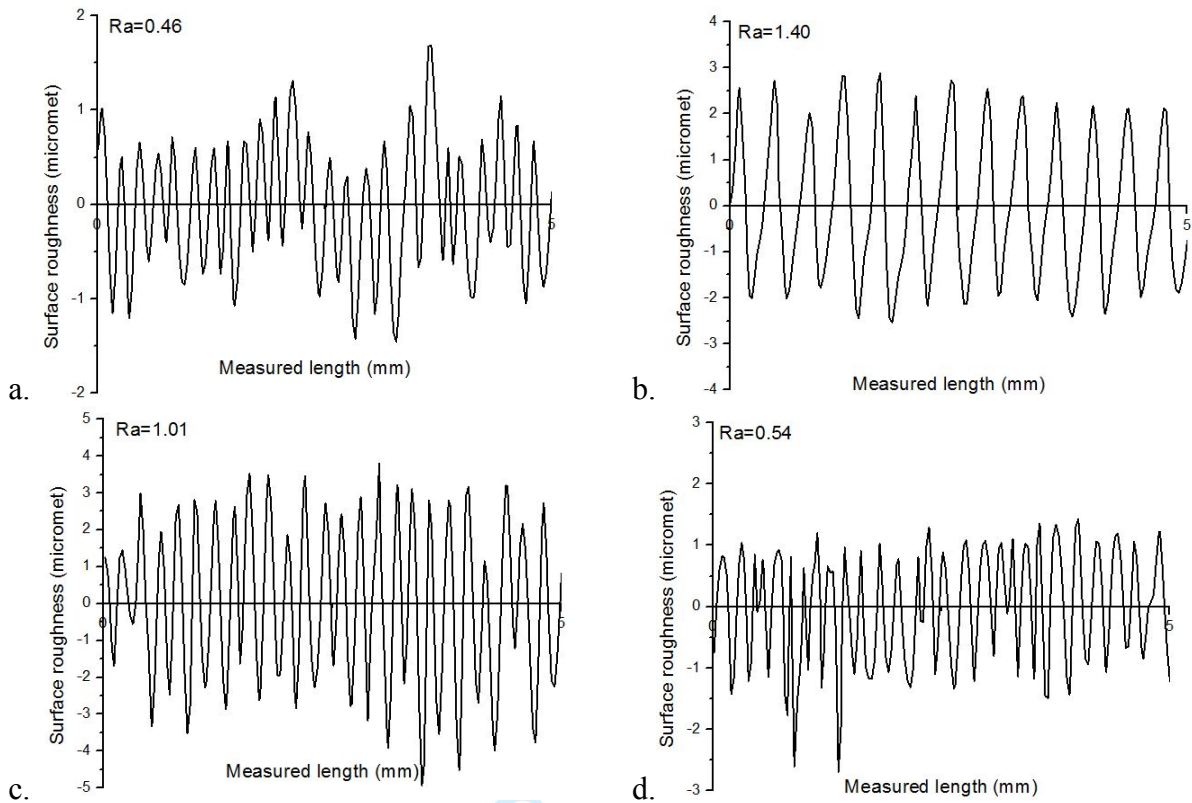


Figure 5. Surface roughness at various machining conditions:  
(a) Experiment no. 1 (Replication-2), (b) Experiment no. 11 (Replication-3),  
(c) Experiment no. 16 (Replication-4), (d) Experiment no. 21 (Replication-3)

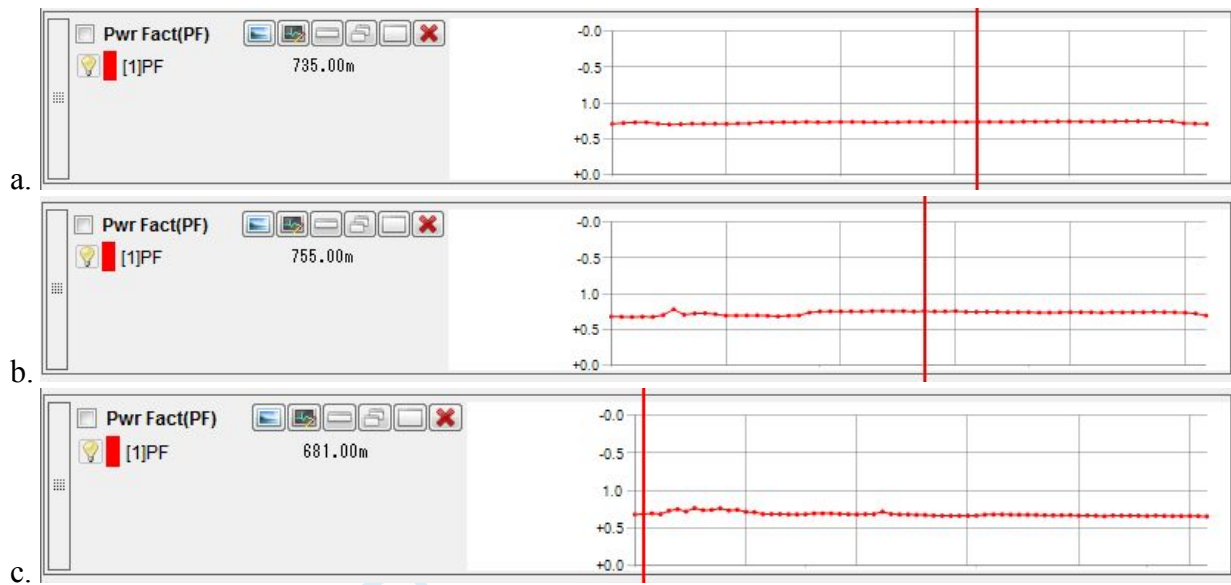


Figure 6. The variations of the power factor at various machining conditions:  
(a) Experiment no. 11 (Replication-3), (b) Experiment no. 20 (Replication-3),  
(c) Experiment no. 24 (Replication-2)

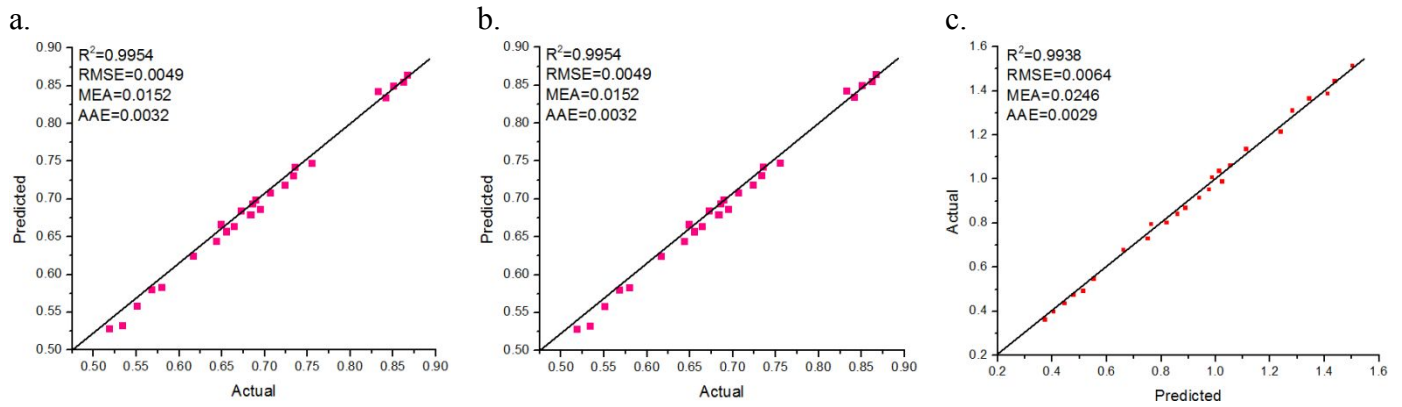


Figure 7. Investigation of adequacy of RBF models: (a) Power factor, (b) Energy consumption, (c) Surface roughness

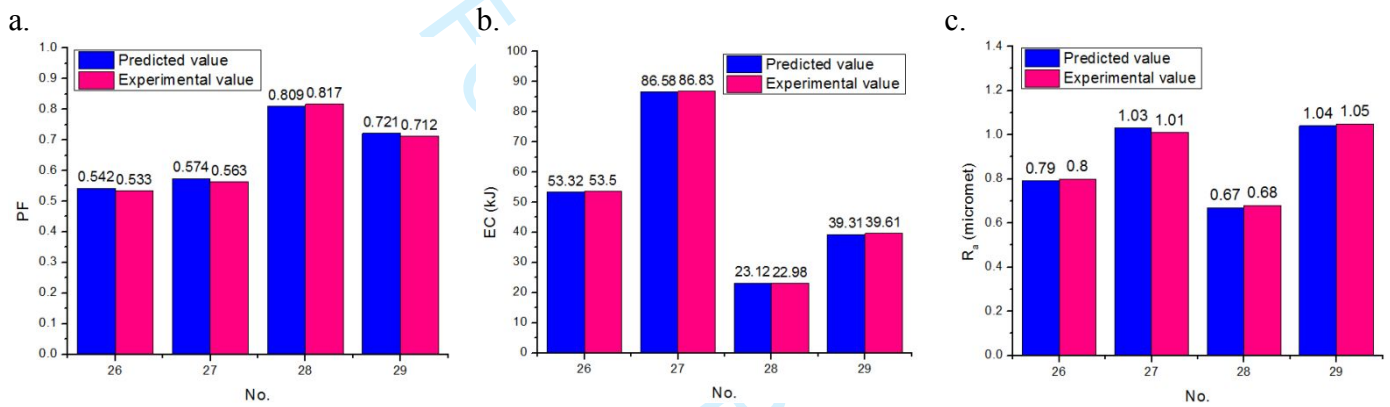


Figure 8. Validation of the accuracy for RBF models: (a) PF model, (b) EC model, (c) SR model

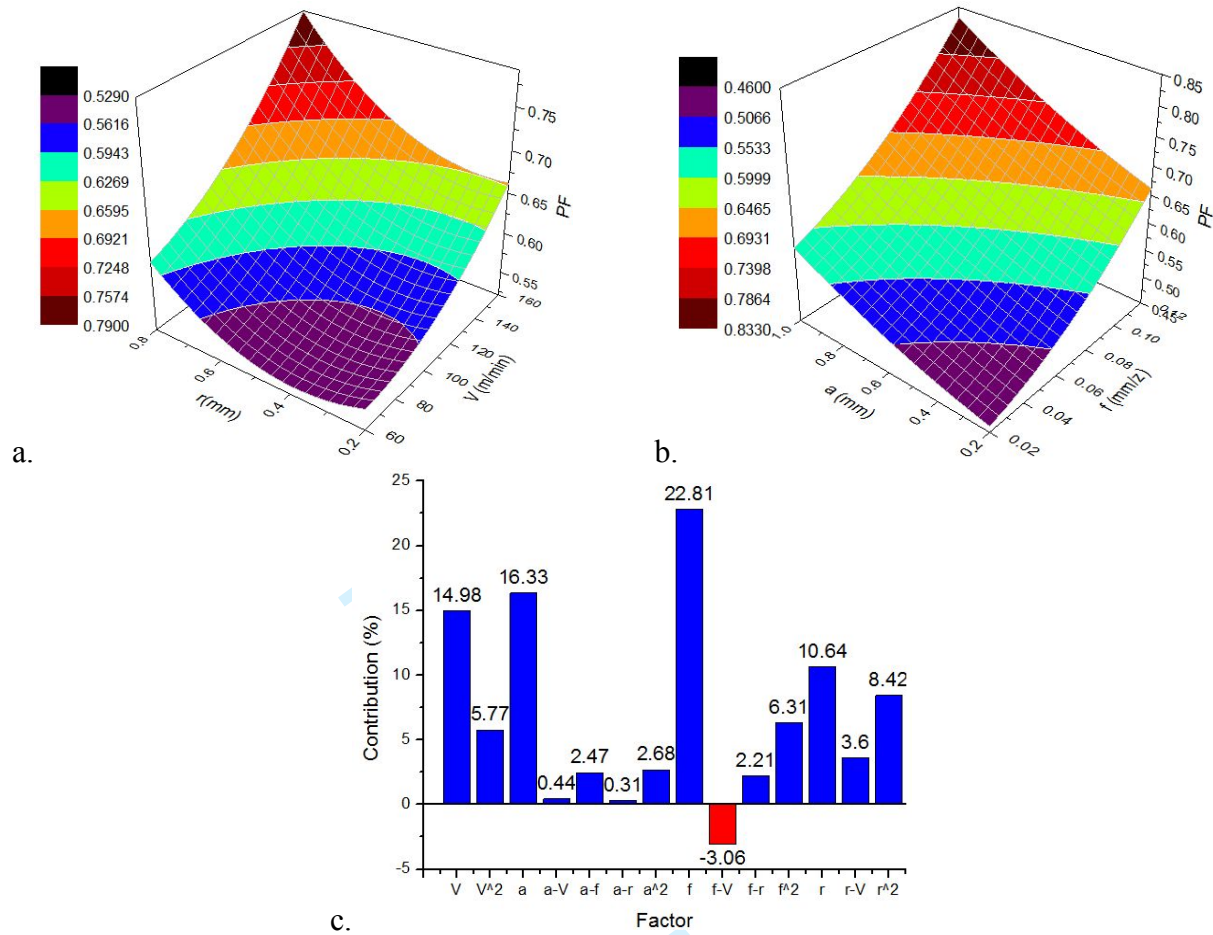


Figure 9. The effects of machining parameters on the PF model: (a) PF versus V and r, (b) PF versus a and f, (c) Parameter contributions for the PF model

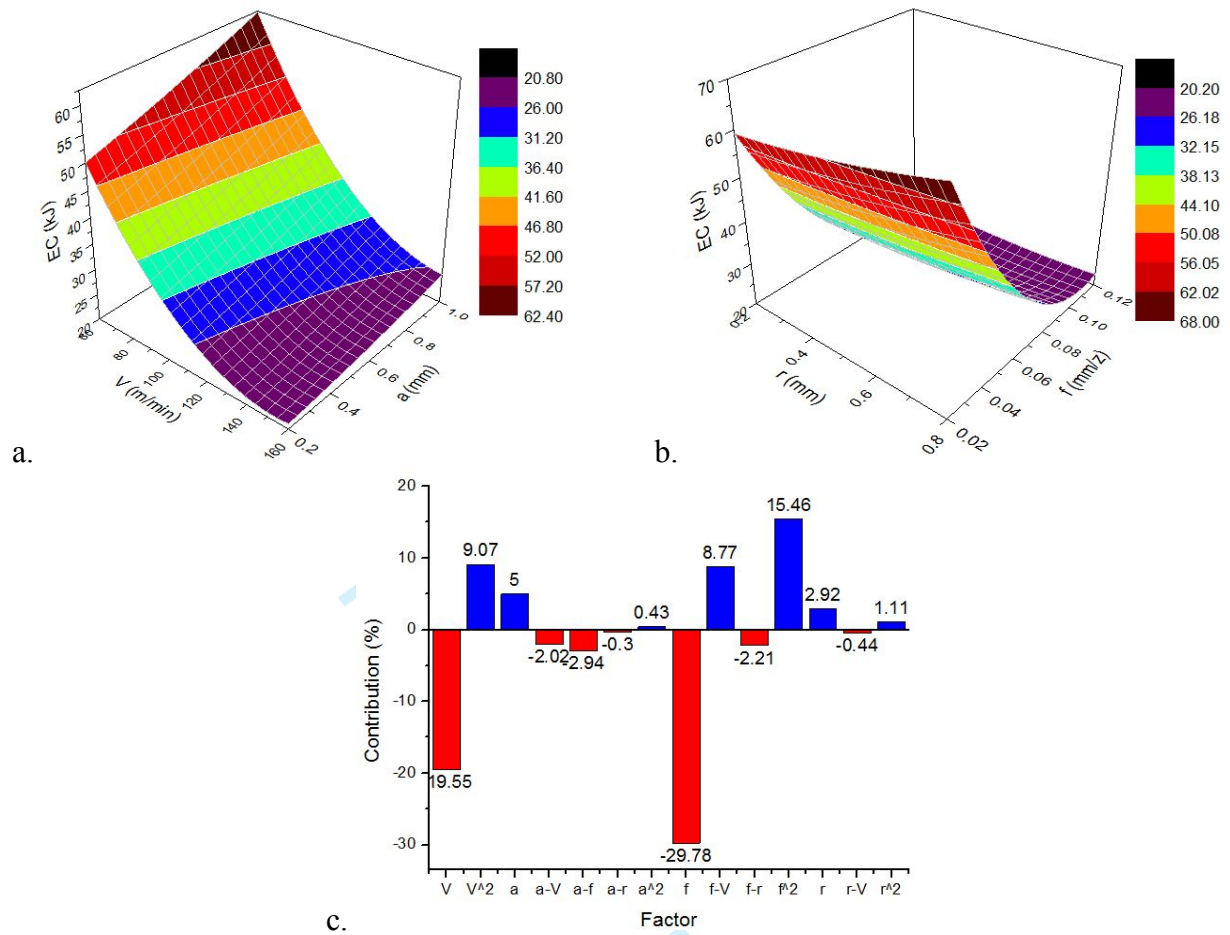


Figure 10. The effects of machining parameters on the EC model: (a) EC versus V and a, (b) EC versus r and f, (c) Parameter contributions for the EC model


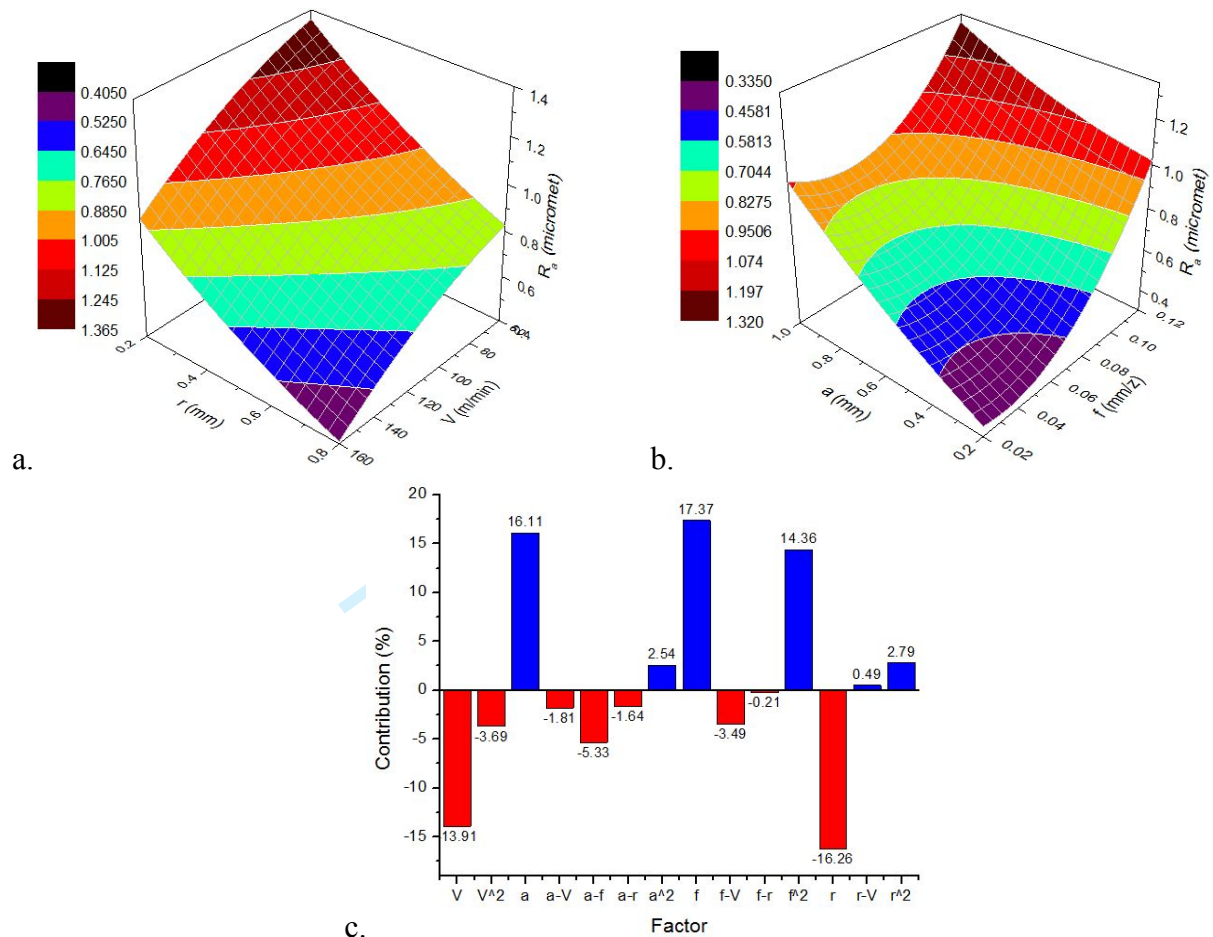



Figure 11. Interaction effects of machining parameters on the  $R_a$  model: (a)  $R_a$  versus  $r$  and  $V$ , (b)  $R_a$  versus  $f$  and  $a$ , (c) Parameter contributions on the  $R_a$  model



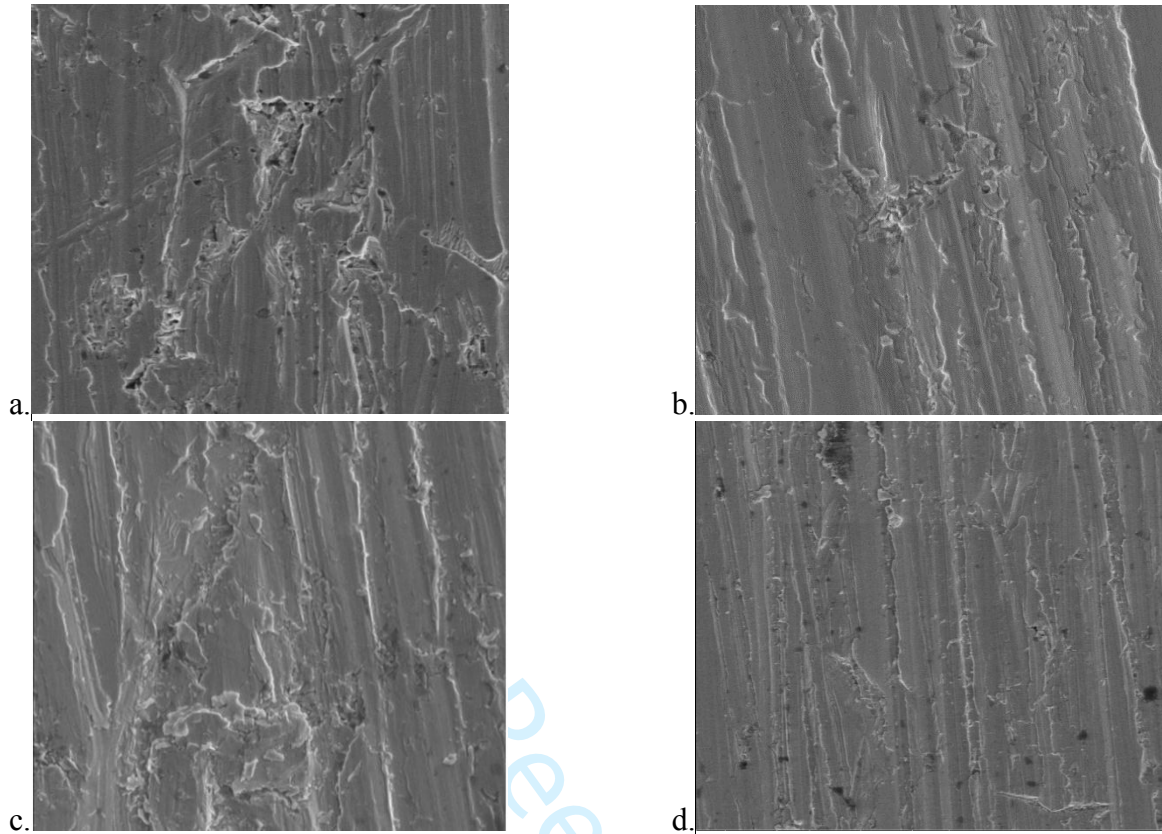


30  
31  
32  
33  
34

Figure 12. SEM of surface morphology at various conditions: (a) Experiment no. 4, (b) Experiment no.12, (c) Experiment no.1, (d) Experiment no. 7

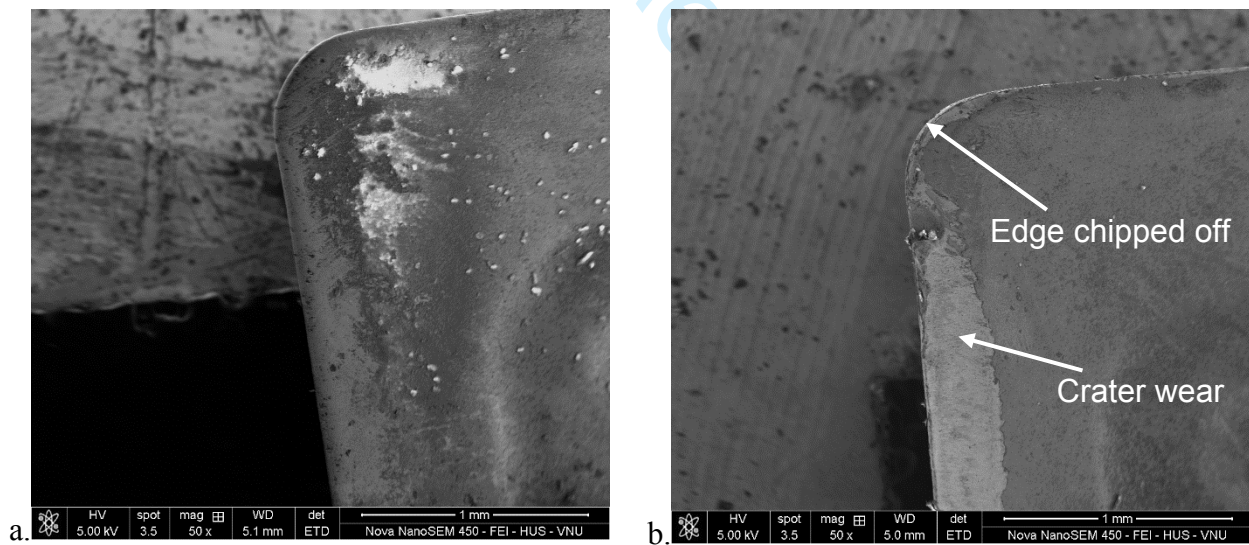


52  
53  
54  
55  
56  
57  
58  
59  
60

Figure 13. SEM images of the worn tool's rake surface at various machining conditions: (a) Experiment no. 16, (b) Experiment no. 20

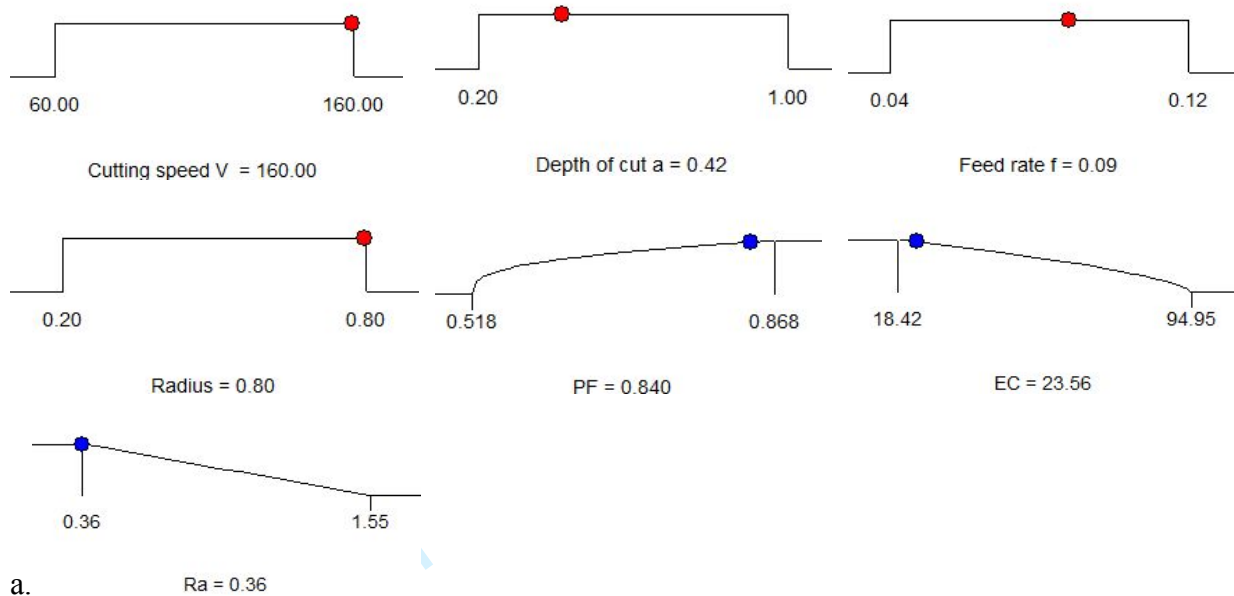


a.

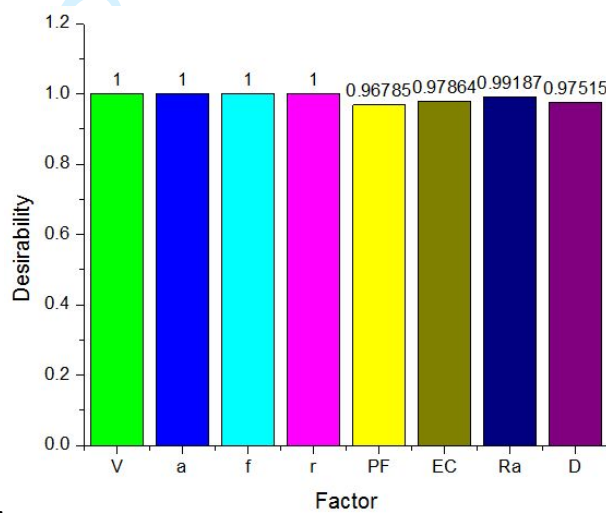

b.

Figure 14. Optimization results generated by DA: (a) Optimal values, (b) Bar graph of the desirability

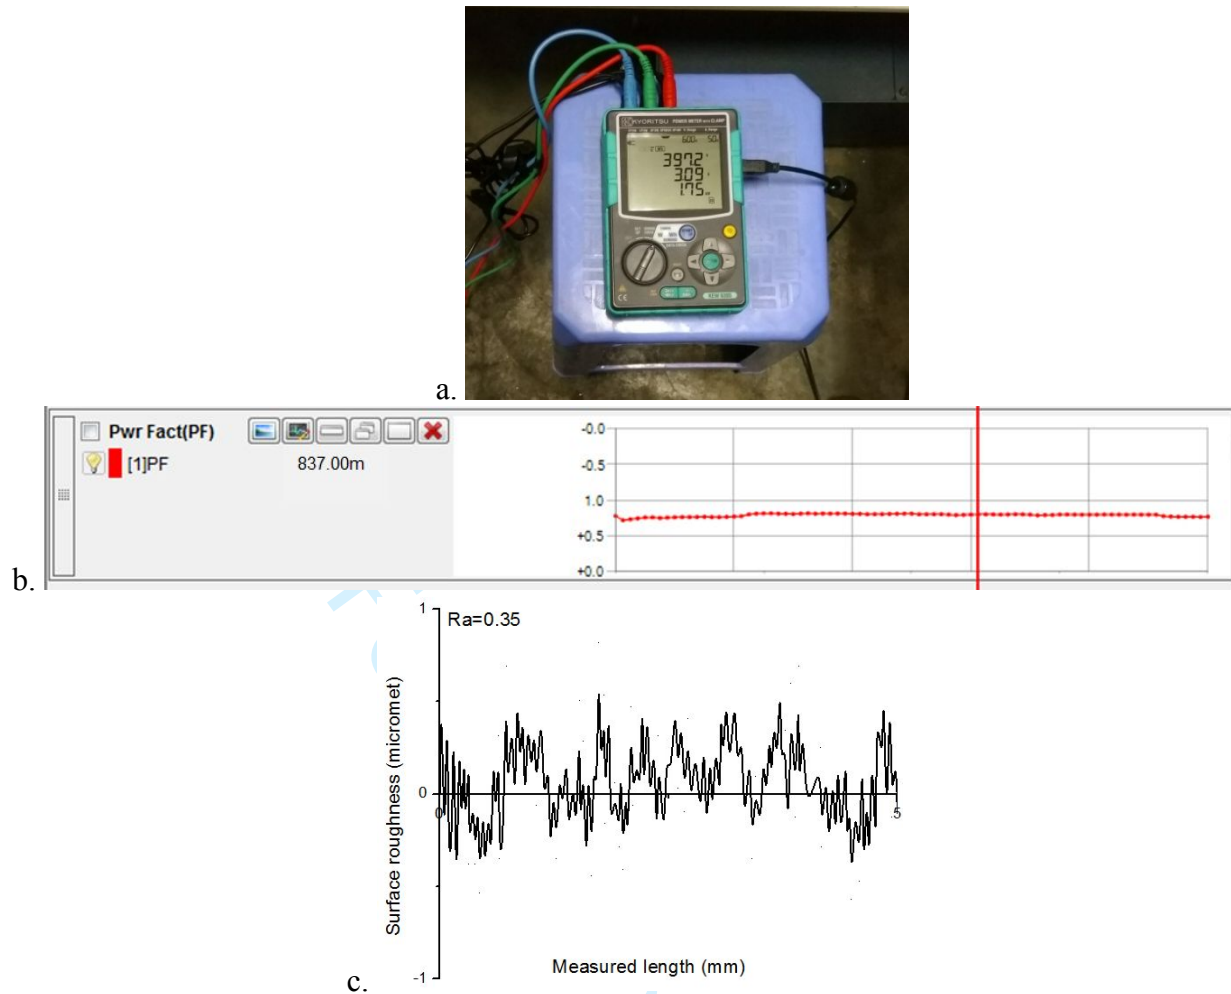

**List of Tables**

Table 1. Processing conditions

Table 2. Experimental results

Table 3. The values of evaluating criteria

Table 4. Pre-processed and deviation results

Table 5. Values of grey relational coefficients (GRC)

Table 6. Eigenvalues and proportions of the principal components

Table 7. Eigenvectors and contributions for the principal components

Table 8. Optimization results

Table 9. Results of confirmatory experiment

Table 1. Processing conditions

Symbol	Parameters	level-1	level 0	level +1
V	Cutting speed (m/min)	60	110	160
a	Depth of cut (mm)	0.2	0.6	1.0
f	Feed rate (mm/z)	0.04	0.08	0.12
r	Nose radius (mm)	0.2	0.4	0.8

Table 2. Experimental results

No.	Cutting speed V (m/min)	Depth of cut a (mm)	Feed rate f (mm/z)	Nose radius r (mm)	Power factor PF	Energy consumption EC (kJ)	Surface roughness $R_a$ ( $\mu\text{m}$ )
1	110	0.2	0.04	0.4	0.518	50.33	0.45
2	110	0.6	0.12	0.8	0.867	25.46	1.08
3	110	0.6	0.08	0.4	0.652	31.56	0.85
4	60	0.6	0.08	0.2	0.611	53.66	1.34
5	160	0.6	0.12	0.4	0.851	18.42	0.95
6	60	0.6	0.12	0.4	0.736	42.6	1.47
7	110	0.2	0.12	0.4	0.690	21.99	1.14
8	60	0.6	0.08	0.8	0.685	59.13	0.78
9	60	1.0	0.08	0.4	0.703	61.68	1.31
10	110	1.0	0.12	0.4	0.868	26.72	1.49
11	110	1.0	0.08	0.2	0.732	35.41	1.42
12	160	0.6	0.08	0.2	0.719	22.84	0.89
13	160	1.0	0.08	0.4	0.835	27.26	0.79
14	60	0.2	0.08	0.4	0.547	48.96	0.82
15	160	0.6	0.04	0.4	0.690	44.62	0.47
16	110	0.6	0.04	0.2	0.566	54.03	0.98
17	60	0.6	0.04	0.4	0.529	94.95	0.82
18	110	1.0	0.04	0.4	0.659	63.82	1.06
19	160	0.2	0.08	0.4	0.671	22.07	0.41
20	110	0.6	0.12	0.2	0.752	23.74	1.55
21	110	0.6	0.04	0.8	0.648	62.35	0.52
22	160	0.6	0.08	0.8	0.862	26.68	0.36
23	110	0.2	0.08	0.2	0.576	28.23	0.91
24	110	0.2	0.08	0.8	0.681	32.95	0.48
25	110	1.0	0.08	0.8	0.843	39.02	0.89
26	80	0.4	0.06	0.4	0.533	53.50	0.45
27	100	0.8	0.02	0.4	0.563	86.83	1.08
28	130	0.5	0.10	0.8	0.817	22.98	0.85
29	150	0.9	0.05	0.2	0.712	39.61	1.34

Table 3. The values of evaluating criteria

Responses	R <sup>2</sup>	RMSE	MEA	AAE
PF	0.9954	0.0049	0.0152	0.0032
EC	0.9921	0.0076	0.0178	0.0046
R <sub>a</sub>	0.9938	0.0064	0.0166	0.0039

Table 4. Pre-processed and deviation results

No.	Pre-processed data $x_i(k)$			Deviation sequences $\Delta_{0i}(k)$		
	Power factor PF	Energy consumption EC	Surface roughness R <sub>a</sub>	Power factor PF	Energy consumption EC	Surface roughness R <sub>a</sub>
1	0.00	0.58	0.92	1.00	0.42	0.08
2	1.00	0.91	0.39	0.00	0.09	0.61
3	0.38	0.83	0.59	0.62	0.17	0.41
4	0.27	0.54	0.18	0.73	0.46	0.82
5	0.95	1.00	0.50	0.05	0.00	0.50
6	0.62	0.68	0.07	0.38	0.32	0.93
7	0.49	0.95	0.34	0.51	0.05	0.66
8	0.48	0.47	0.65	0.52	0.53	0.35
9	0.53	0.43	0.20	0.47	0.57	0.80
10	1.00	0.89	0.05	0.00	0.11	0.95
11	0.61	0.78	0.11	0.39	0.22	0.89
12	0.57	0.94	0.55	0.43	0.06	0.45
13	0.91	0.88	0.64	0.09	0.12	0.36
14	0.08	0.60	0.61	0.92	0.40	0.39
15	0.49	0.66	0.91	0.51	0.34	0.09
16	0.14	0.53	0.48	0.86	0.47	0.52
17	0.03	0.00	0.61	0.97	1.00	0.39
18	0.40	0.41	0.41	0.60	0.59	0.59
19	0.44	0.95	0.96	0.56	0.05	0.04
20	0.67	0.93	0.00	0.33	0.07	1.00
21	0.37	0.43	0.87	0.63	0.57	0.13
22	0.98	0.89	1.00	0.02	0.11	0.00
23	0.17	0.87	0.54	0.83	0.13	0.46
24	0.47	0.81	0.90	0.53	0.19	0.10
25	0.93	0.73	0.55	0.07	0.27	0.45

Table 5. Values of grey relational coefficients (GRC)

No.	Grey relation coefficient		
	Power factor PF	Energy consumption EC	Surface roughness $R_a$
1	0.33	0.55	0.87
2	1.00	0.84	0.45
3	0.45	0.74	0.55
4	0.41	0.52	0.38
5	0.91	1.00	0.50
6	0.57	0.61	0.35
7	0.50	0.91	0.43
8	0.49	0.48	0.59
9	0.51	0.47	0.39
10	1.00	0.82	0.34
11	0.56	0.69	0.36
12	0.54	0.90	0.53
13	0.84	0.81	0.58
14	0.35	0.56	0.56
15	0.50	0.59	0.84
16	0.37	0.52	0.49
17	0.34	0.33	0.56
18	0.46	0.46	0.46
19	0.47	0.91	0.92
20	0.60	0.88	0.33
21	0.44	0.47	0.79
22	0.96	0.82	1.00
23	0.37	0.80	0.52
24	0.48	0.72	0.83
25	0.87	0.65	0.53

Table 6. Eigenvalues and proportions of the principal components

Principal component	Eigen values	Proportion (%)
First	1.5614	52.00
Second	0.9973	33.20
Third	0.4412	14.70

Table 7. Eigenvectors and contributions for the principal components

Characteristics	Eigenvectors			Weight value
	The first principal component	The second principal component	The third principal component	
PF	0.706	0.013	-0.708	0.32
EC	0.695	0.179	0.696	0.35
$R_a$	-0.135	0.984	-0.117	0.33

Table 8. Optimization results

Method	Optimization parameters				Responses		
	Cutting speed V (m/min)	Depth of cut a (mm)	Feed rate f (mm/z)	Nose radius r (mm)	Power factor PF	Energy consumption EC (kJ)	Surface roughness R <sub>a</sub> (μm)
Initial	110	0.60	0.08	0.4	0.652	31.56	0.85
DA	160	0.42	0.09	0.8	0.840	20.56	0.36
Improvement (%)					28.83	-34.85	-57.65

Table 9. Results of confirmatory experiment

Method	Responses			
	Power factor PF	Power consumption P <sub>c</sub> (W)	Energy consumption EC (kJ)	Surface roughness R <sub>a</sub> (μm)
DA	0.840	1746	20.56	0.36
Confirmatory experiment	0.836	1752	20.63	0.35
Error (%)	0.48	0.34	0.34	2.78